

This item is the archived peer-reviewed author-version of:

Shearing and rotation of β'' and β' precipitates in an Al-Mg-Si alloy under tensile deformation : in-situ and ex-situ studies

Reference:

Yang Mingjun, Orekhov Andrey, Hu Zhi-Yi, Feng Man, Jin Shenbao, Sha Gang, Li Kai, Samaeeaghmiyoni Vahid, Song Min, Du Yong,- Shearing and rotation of β'' and β' precipitates in an Al-Mg-Si alloy under tensile deformation : in-situ and ex-situ studies
Acta materialia - ISSN 1873-2453 - 220(2021), 117310
Full text (Publisher's DOI): <https://doi.org/10.1016/J.ACTAMAT.2021.117310>
To cite this reference: <https://hdl.handle.net/10067/1825280151162165141>

Acta Materialia

Shearing and rotation of β'' and β' precipitates in an Al-Mg-Si alloy under tensile deformation: In-situ and ex-situ studies

--Manuscript Draft--

Manuscript Number:	A-21-2047R1
Article Type:	Full length article
Keywords:	Precipitate; Fragments; interface; Dislocation-precipitate interaction; TEM
Corresponding Author:	Kai Li, Ph.D State Key Laboratory of Powder Metallurgy, Central South University, Changsha 410083, China Changsha, CHINA
First Author:	Mingjun Yang
Order of Authors:	Mingjun Yang Andrey Orekhov Zhi-Yi Hu Man Feng Shenbao Jin Gang Sha Kai Li, Ph.D Vahid Samaee Min Song Yong Du Gustaaf Van Tendeloo Dominique Schryvers
Abstract:	<p>The interaction between dislocations and nano-precipitates during deformation directly influences hardening response of precipitation-strengthening metals such as Al-Mg-Si alloys. However, how coherent and semi-coherent nano-precipitates accommodate external deformation applied to an Al alloy remains to be elucidated. In-situ tensile experiments in a transmission electron microscope (TEM) were conducted to study the dynamic process of dislocations cutting through coherent needle-like β'' precipitates with diameters of 3~8 nm. Comprehensive investigations using in-situ , ex-situ TEM and atom probe tomography uncovered that β'' precipitates were firstly sheared into small fragments, and then the rotation of the fragments, via sliding along precipitate/matrix interfaces, destroyed their initially coherent interface with the Al matrix. In contrast, semi-coherent β' precipitates with sizes similar to β'' were more difficult to be fragmented and accumulation of dislocations at the interface increased interface misfit between β' and the Al matrix. Consequently, β' precipitates could basically maintain their needle-like shape after the tensile deformation. This research gains new insights into the interaction between nano-precipitates and dislocations.</p>

[Click here to view linked References](#)

1 Shearing and rotation of β'' and β' precipitates in an Al-Mg-Si alloy 2 3 4 5 6 7 8 9 10 11 12 13 14 15 16 17 18 19 20 21 22 23 24 25 26 27 28 29 30 31 32 33 34 35 36 37 38 39 40 41 42 43 44 45 46 47 48 49 50 51 52 53 54 55 56 57 58 59 60 61 62 63 64 65

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Mingjun Yang^{1, †}, Andrey Orekhov^{2, †}, Zhi-Yi Hu^{3, 4}, Man Feng⁵, Shenbao Jin⁵, Gang Sha⁵, Kai Li^{1, 6, *}, Vahid Samaee², Min Song^{1, 6}, Yong Du^{1, 6}, Gustaaf Van Tendeloo^{2, 4},
Dominique Schryvers²

¹State Key Laboratory of Powder Metallurgy, Central South University, Changsha 410083, China

²Electron Microscopy for Materials Science (EMAT), University of Antwerp, Antwerp B-2020,

Belgium

³State Key Laboratory of Advanced Technology for Materials Synthesis and Processing, Wuhan

University of Technology, Wuhan 430070, China

⁴NRC (Nanostructure Research Centre), Wuhan University of Technology, Wuhan 430070, China

⁵Herbert Gleiter Institute of Nanoscience, Nanjing University of Science and Technology, Nanjing

210094, China

⁶Advanced Research Center, Central South University, Changsha 410083, China

Abstract

The interaction between dislocations and nano-precipitates during deformation directly influences hardening response of precipitation-strengthening metals such as Al-Mg-Si alloys. However, how coherent and semi-coherent nano-precipitates accommodate external deformation applied to an Al alloy remains to be elucidated. *In-situ* tensile experiments in a transmission electron microscope (TEM) were conducted to study the dynamic process of dislocations cutting through coherent needle-like β'' precipitates with diameters of 3~8 nm. Comprehensive investigations using *in-situ*, *ex-situ* TEM and atom probe tomography uncovered that β'' precipitates

1 were firstly sheared into small fragments, and then the rotation of the fragments, via
2 sliding along precipitate/matrix interfaces, destroyed their initially coherent interface
3 with the Al matrix. In contrast, semi-coherent β' precipitates with sizes similar to β''
4 were more difficult to be fragmented and accumulation of dislocations at the interface
5 increased interface misfit between β' and the Al matrix. Consequently, β' precipitates
6 could basically maintain their needle-like shape after the tensile deformation. This
7 research gains new insights into the interaction between nano-precipitates and
8 dislocations.

9
10 Key words: Precipitate; Fragments; Interface; Dislocation-precipitate interaction;
11 TEM

12 †The two authors contribute to the work equally

13 *Corresponding authors. Tel: + 86 18973163497; email: leking@csu.edu.cn (K. Li);
14

1. Introduction

Precipitation of secondary phases plays a critical role in the mechanical properties of many alloys [1]. Densely distributed fine precipitates can cause precipitation strengthening by pinning gliding dislocations. Precipitation strengthening of Al-Mg-Si alloys has been intensively investigated since they are widely used in, e.g., the lightweight automobile industry. The precipitation sequence of Al-Mg-Si alloys is widely accepted as [2, 3]: super-saturated solid solution (SSSS) \rightarrow atomic clusters \rightarrow GP zones \rightarrow β'' \rightarrow β' , U1, U2, B' \rightarrow β , Si. Among these precipitates, β'' and β' are seen as coherent and semi-coherent precipitates, providing the largest and the second large contributions to alloy strength, respectively [4-7]. The mechanical properties of Al-Mg-Si based alloys are mainly determined by the impeding effect of precipitates on slide of dislocations, and precipitates are generally sheared or bypassed by gliding dislocations [7-15]. In addition to the inherent elastic properties (e.g., elastic modulus) and lattice misfit between the precipitate and matrix, the radius of a precipitate affects whether it can be sheared or bypassed by a gliding dislocation [16, 17].

Critical radius of precipitates r_c has been proposed for the transition from shearing to bypassing, but no precise value of r_c for β'' has been unanimously accepted by previous investigations. For instance, it was assumed to be 3.0 nm for a needle-like shape according to Esmaeili et al. [18], or 5.0 nm for an assumed spherical shape (for simplification) according to Myhr et al. [19]. Further *ex-situ* investigations on deformed Al-Mg-Si-Cu alloys have shown that needle-like β'' precipitates with a radius range from 1.8 nm to 2.5 nm can be sheared by dislocations [13, 20], while some other work

1 pointed out that β'' precipitates are shearable regardless of their size [13, 14]. This
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

1 pointed out that β'' precipitates are shearable regardless of their size [13, 14]. This
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

5 Dislocation shearing can drastically change the morphologies and orientations of
6 precipitates. For example, it has been reported that both needle-like MgZn_2 (diameter
7 ~ 70 nm) and plate-like $\theta\text{-Al}_2\text{Cu}$ (thickness ~ 8 nm and width of several hundred nm)
8 precipitates in aluminum alloys can be fragmented into very small spherical particles
9 during equal-channel angular pressing (ECAP) [21, 22], and the observed
10 polycrystalline diffraction rings of precipitates revealed their rotation alongside
11 dislocation shearing. Besides, the gliding of dislocations inside the semi-coherent plate-
12 like precipitates (thickness ~ 11 nm) in a two-phase Ni-Co superalloy was found to cause
13 rotation of its central part, which was oppositely sheared between two positions where
14 the distance was smaller than the precipitate thickness [23]. The corresponding shift
15 was as large as half the thickness of the precipitate. It should be noted that residual
16 dislocations were produced at the entrance and exit sites of the principal shear at the
17 initial state of deformation, and their Burgers vectors are different from that of the
18 matrix or the precipitate. Furthermore, the interaction between these residual
19 dislocations with the secondary shear created stacking faults within the precipitate. The
20 accumulation of stacking faults leads to the rotation of the central part of the precipitate.
21 In their work [23], the rotated central part and the un-rotated remaining parts were still
22 connected, i.e. the precipitate was not broken-apart.

1 As for fine needle-like precipitates, e.g. those with diameters smaller than 10 nm
2 in Al-Mg-Si alloys, little is known about their behaviors after dislocations start to shear
3 them. β'' precipitates under shearing of dislocations in 20% compressed Al-Mg-Si
4 samples have been studied by scanning precession electron diffraction (SPED) [24, 25].
5 The results show that β'' precipitates were sheared by multiple gliding dislocations in
6 single matrix Burgers vector steps. The shear planes were proposed to be the same as
7 the matrix glide planes $\{111\}_{Al}$, and the precipitates were not found to be rotated even
8 after being fragmented into discrete parts. What will happen to needle-like β''
9 precipitates during continuous plastic deformation until fracture (probably stronger
10 than 20% compression), and whether they can be sheared into very small parts and
11 rotated or not, should be studied in detail. Similar knowledge for needle-like β'
12 precipitates is also important but missing. The information is of significance in
13 advancing our understanding about the plastic deformation mechanisms of many types
14 of precipitation strengthened materials, which determines the ultimate tensile strength.

15 In present work, *ex-situ* and *in-situ* TEM technical are applied to study the
16 interaction between dislocations and both β'' and β' precipitates. *In-situ* tensile
17 experiments in TEM allow direct observations of the dynamical microstructural
18 evolution during deformation, and are thus used in our work. Modern *in-situ* TEM
19 holders developed in recent years use microelectromechanical system (MEMS) devices
20 that allow researchers to perform tensile experiments on microscale single crystal
21 samples along controlled orientations and with controlled load or displacement, which
22 is, a.o., very helpful for understanding samples with nanoscale precipitates. However,

1 in most *in-situ* TEM holders, the sample can only be tilted along one axis (parallel to
2 the tensile direction) and observations of precipitates along another crystallographic
3 direction (usually required) is not easy, thus supplementary *ex-situ* observations are still
4 of key importance.

5 The purposes of this work are twofold: (1) to investigate the shearing behaviors
6 and possible rotation behaviors of coherent β'' and semi-coherent β' precipitates during
7 the plastic stage of tensile deformation, (2) to understand the rotation mechanisms of
8 β'' and β' precipitates (if happened). In this work, we combine the advantages of both
9 *in-situ* and *ex-situ* observations in TEM to investigate the evolution of β'' and β'
10 precipitates during the tensile deformation process of an Al-Mg-Si alloy. Atom probe
11 tomography (APT) analysis was used to reveal the morphologies and spatial
12 distribution of both β'' and β' precipitates in deformed samples.

13 **2. Methods**

14 An Al-0.66%Mg-0.41%Si (wt.%) alloy with 0.11% Fe impurities, in the form of
15 1 mm thick sheets, was used for experimental investigations here. The sheets were
16 solution heat treated at 550°C for 30 min, water quenched and aged at 180°C for 2 h, 3
17 h or 6 h, followed by air cooling.

18 *Ex-situ* tensile experiments were performed on an Instron 3369 testing machine
19 (with extensometer) at room temperature and at a constant crosshead speed of 5
20 mm/min. The tensile samples with a gauge length of 25.0 mm and a width of 6.0 mm
21 were cut from the 1.0 mm thick rolled sheets, and their long axes were parallel to the
22 rolling direction.

1 For *ex-situ* observations of macroscopic tensile samples, TEM thin foils were
2 prepared by electropolishing using a Tenupol 5 machine (Struers) with 30% nitric acid
3 and 70% methanol solution at -30 ~ -35°C. It should be noted that the preparation of
4 *ex-situ* TEM samples near the fracture region was achieved by placing a fractured
5 sample between two $\Phi 3$ mm platinum plates, each with a $\Phi 1$ mm hole in the center (a
6 schematic diagram is shown in Fig. S1 in the Supplementary Document). The centers
7 of the $\Phi 1$ mm holes were located 0.5 - 1.5 mm away from the fracture tips of tensile-
8 deformed samples. As the polished hole on the sample closest to the fracture tip is as
9 large as $\Phi 0.6$ mm, the observed thin area is very close to the edge of the $\Phi 1$ mm area,
10 i.e., about 0.2 - 1.2 mm away from the tip.

11 For *in-situ* tensile experiments, two samples of the alloy aged for 3 h were prepared
12 by the method first developed by Samee et al. [26]. In the first step, a suitable grain
13 with a preferred orientation $[5\bar{1}2]_{Al}$ was selected in a TEM from the thin areas of several
14 electropolished samples. Then two parallel dog-bone samples along $[021]_{Al}$ direction
15 were cut by FIB in a FEI Helios Nanolab 650i instrument and mounted on two push to
16 pull (PTP) devices compatible for a Bruker Inc. PI-95 TEM picoIndenter (*in-situ*
17 mechanical test holder). One is for measuring the stress-strain curve and the other for
18 high-magnification observations. During the cutting and mounting procedures, the
19 central area of every tensile sample was protected from illuminating with the ion beam,
20 such as to minimize the effects of beam damage.

21 *In-situ* tensile experiments were performed on a FEI Osiris microscope in bright-
22 field TEM mode operating at 200 kV with a beam current of about 2 nA. A 100 μm

1 1 conductive diamond flat puncher indenter of the single-tilt PI 95 TEM PicoIndenter
2
3 2 was used. Tensile experiments were performed in the load control mode with a loading
4
5
6 3 rate of 0.2 $\mu\text{N}/\text{sec}$. The net applied force on the specimen was determined by subtracting
7
8
9 4 the contribution of the spring stiffness from the raw force. The thickness of the first
10
11
12 5 sample was measured as 119.9 ± 3.6 nm by convergent beam electron diffraction
13
14 6 (CBED) [27] before *in-situ* tension. This dogbone sample was observed in low
15
16
17 7 magnification to ensure that the two ends are kept in the field of view. The second
18
19
20 8 sample was not used for mechanical property measurements (thus sample thickness was
21
22
23 9 not measured) and the tensile experiment was carried out at higher magnifications so
24
25
26 10 that the interaction between precipitates and dislocations could be observed *in-situ*.

27
28 11 *Ex-situ* TEM observations such as selected area electron diffraction (SAED),
29
30
31 12 bright field (BF) and dark field (DF) imaging as well as high-resolution TEM (HRTEM)
32
33
34 13 were performed using a FEI Tecnai G2 F20 S-Twin transmission electron microscope
35
36
37 14 operating at 200 kV. High angle angular dark field-scanning transmission electron
38
39
40 15 microscopy (HAADF-STEM) and elemental mapping using energy-dispersive X-rays
41
42 16 (EDX) spectroscopy were performed on a FEI Titan 80–300 Themis microscope
43
44
45 17 operating at 300 kV, which is equipped with both probe and image aberration correctors
46
47
48 18 and a Super-X windowless EDX detector.

49
50 19 APT was used to analyze the precipitates in the area about 2.3 mm away from the
51
52
53 20 fracture tip of the tensile-tested sample which was aged for 6 h. The APT sample was
54
55
56 21 prepared by two-step standard electropolishing procedures [28]. The first step was
57
58
59 22 carried out in an electrolyte of 30 vol.% perchloric acid in acetic acid at 22 V and the

1 second step was carried out in an electrolyte of 5% perchloric acid in 2-butoxyethanol
2
3 at 20 V. APT was performed on a LEAP-4000XSi instrument at 40 K (-233°C) with a
4
5 pulse repetition rate of 200 kHz and a detection rate of 0.5%. The pulse energy was 80
6
7 pJ. APT data were reconstructed using IVAS 3.6.8 software with a voltage range of
8
9 1500-4800 V. The precipitates were determined with iso-surfaces at 3.0 at.% Si.
10
11
12

13 **3. Results**

14 **3.1 Quantitative characterizations of the precipitates**

15 The undeformed microstructure of the Al-Mg-Si alloy aged for 3 h, is shown in Fig.
16
17 1. BF images clearly show uniformly distributed β'' precipitates elongated along
18
19 $\langle 100 \rangle_{\text{Al}}$ directions (see Fig. 1a). The average length (l) of 500 precipitates was
20
21 measured as 26.4 ± 1.2 nm (average value \pm standard deviation, as used throughout the
22
23 whole paper). The SAED pattern shows, in addition to bright diffraction spots from the
24
25 matrix crystal, the presence of extra spots with relatively weak intensity (Fig. 1b). These
26
27 spots originate from β'' precipitates according to the diffraction pattern simulation by
28
29 Li et al. [29], i.e. the precipitates in this alloy are mainly β'' .
30
31
32
33
34
35
36
37
38
39
40
41

42 Figure 1c shows a HRTEM image of a β'' precipitate, which was identified from
43
44 the corresponding Fast Fourier transform (FFT) pattern (Fig. 1c inset). The average
45
46 cross-section area (A_{CS}) of the precipitates was measured in 60 HRTEM images and the
47
48 obtained value of A_{CS} is 28.7 ± 1.7 nm². By taking the real needle-like morphology of
49
50 β'' , $r_{\text{needle-3h}}$ was calculated by the equation $A_{\text{CS}} = \pi \cdot r_{\text{needle-3h}}^2$ as 3.0 ± 0.09 nm. In the
51
52 same way (details can be seen in Fig. S2 in the Supplementary Document), we obtained
53
54 the value of the average radius of precipitates in the alloy aged for 2 h ($r_{\text{needle-2h}}$) as 2.18
55
56
57
58
59
60
61
62
63
64
65

1 ± 0.11 nm, and the needle-like precipitates in this sample were also found to be mainly
2 β'' . The number densities of precipitates were calculated by a method based on high
3 precision measurement of the thin foil thickness by CBED [27]. The number density of
4 β'' and β' precipitates in the sample aged for 6 h were reported, in our previous work
5 [30], to be $(1.51 \pm 0.17) \times 10^{22} \text{ m}^{-3}$ and $(1.12 \pm 0.12) \times 10^{22} \text{ m}^{-3}$, respectively. The ratio
6 between these two types of precipitates was evaluated from HRTEM studies of 187
7 precipitates in an area. The values of the average radius of β'' precipitates ($r_{\text{needle-6h-}\beta''}$)
8 and needle-like β' precipitates ($r_{\text{needle-6h-}\beta'}$) were calculated as 2.43 ± 0.08 nm and 2.57
9 ± 0.08 nm, respectively. The precipitate sizes in these 3 samples are listed in Table 1.

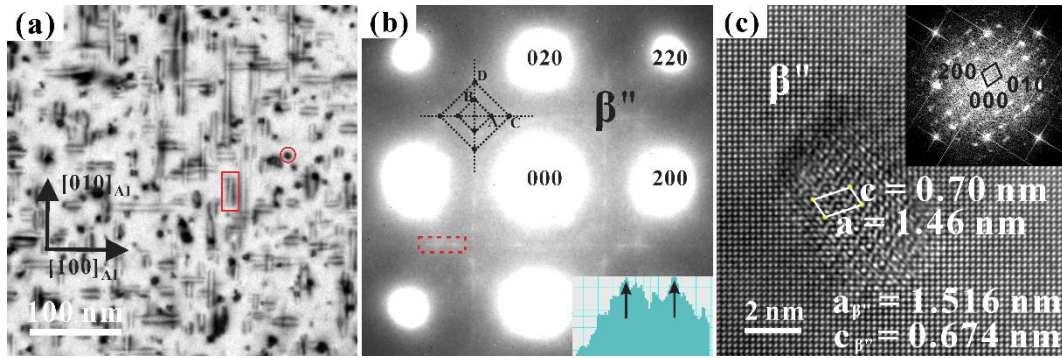



Fig. 1. TEM analysis of the undeformed microstructure of an Al-Mg-Si sample aged for 3 h at 180 °C. (a) BF TEM image, (b) SAED pattern with the intensity profile from the red dotted box inserted, and (c) HRTEM image with corresponding FFT (inset). The electron beam is parallel to $[001]_{\text{Al}}$.

Table 1 Summary of the parameters related to quantitative characterization of the precipitates in the undeformed Al-Mg-Si samples aged at 180°C for 2 h, 3 h and 6 h, respectively. n – number density, V_f - volume fraction.

Parameters	2 h	3 h	6 h ($N_{\beta''} : N_{\beta'} = 103 : 76$)		
			β''	β'	$\beta'' + \beta'$
l (nm)	14.2 ± 0.6	26.4 ± 1.2	26.2 ± 1.3	22.2 ± 3.5	24.5 ± 1.3
A_{CS} (nm ²)	14.9 ± 0.2	28.7 ± 1.7	18.5 ± 1.1	20.7 ± 1.2	19.4 ± 1.2
r (nm)	2.18 ± 0.11	3.02 ± 0.09	2.43 ± 0.07	2.57 ± 0.08	2.49 ± 0.08
n (10^{22} m^{-3})	3.60 ± 0.36	1.21 ± 0.13	1.51 ± 0.17	1.12 ± 0.12	2.63 ± 0.29
V_f (%)	0.76 ± 0.11	0.92 ± 0.10	0.68 ± 0.08	0.57 ± 0.06	1.25 ± 0.14

3.2 In-situ observations of β'' precipitates sheared by gliding dislocations

1 The sample used for the *in-situ* tensile experiment was first cut from an
 2 electropolished thin foil (from the bulk sample aged for 3 h) in a zone axis close to $[5\bar{1}$
 3 $2]_{Al}$ with deviations less than 3° in both α and β tilt angles (of the holder), and its long
 4 axis was approximately along $[021]_{Al}$ with deviations around $\pm 2^\circ$. This deliberate
 5 selection produces a Schmidt factor (m) of 0.49, very close to the upper limit of 0.5
 6 which corresponds to the most smooth dislocation gliding. The details of the *in-situ*
 7 tensile specimen preparation can be seen in Figs. 2a-2e, and Fig. 2f shows the
 8 geometrical schematic of the specimen.

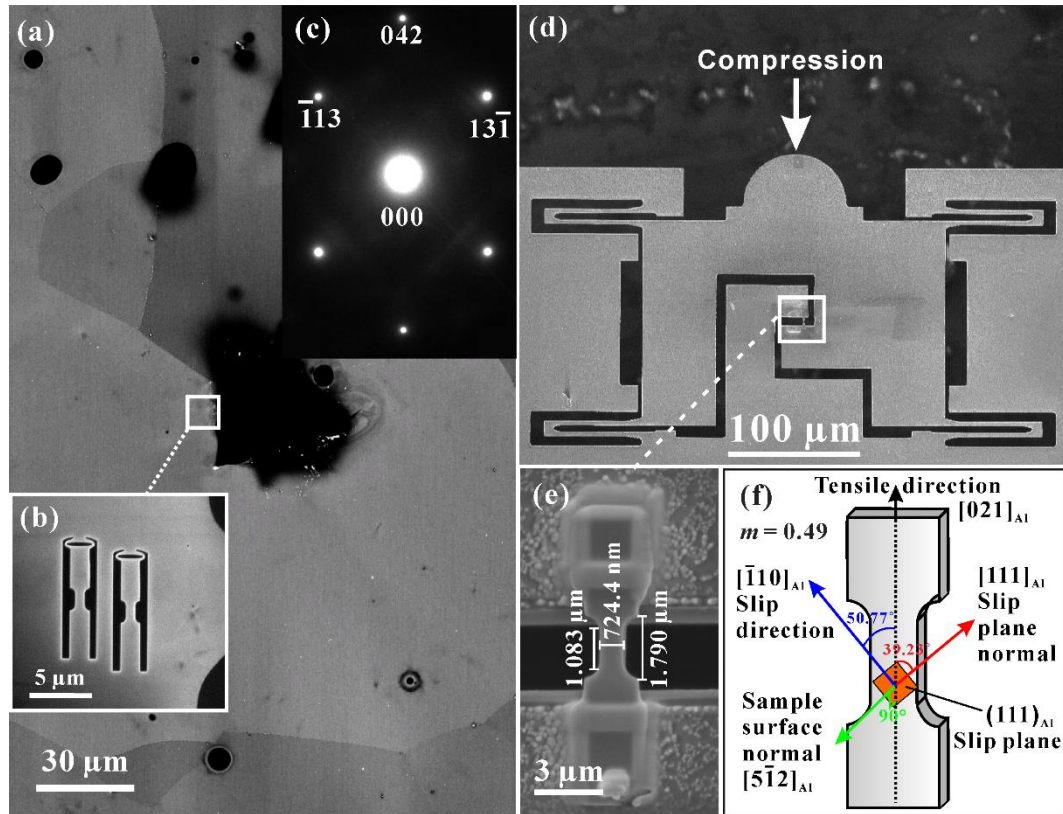

9
 10 **Fig. 2.** Sample details for TEM *in-situ* tensile tests. (a) Back scattered electron (BSE)
 11 image of thin target area of a $\Phi 3$ mm electropolished sample. (b) Enlarged image and
 12 (c) SAED pattern of the grain from which samples for *in-situ* experiments were cut. (d)
 13 BSE image of the PTP chip used for *in-situ* TEM tensile experiments. (e) Magnified
 14 BSE image of the mounted *in-situ* sample and (f) its schematic diagram showing
 15 crystallographic directions.

16 A true stress-strain curve was obtained as shown in Fig. 3a, according to the method

1 described in Ref.[31]. The curve reveals much higher tensile strength and yield strength
2 compared to the macro tensile curves shown in Fig. S3. This may be caused by the
3 reduction in the number of active slip systems and dislocation density in the small size
4 sample prepared for the *in-situ* TEM tensile experiment [32-35]. Needle-like
5 precipitates can be observed in the BF images of Fig. 3b (before the start of the *in-situ*
6 tensile test) and Fig. 3c (during the *in-situ* tensile test). Following the continuous
7 stretching, the *in-situ* specimen fractured in the middle. In order to enable detailed
8 observations of the fracture tips, the stress was kept large enough to avoid collision
9 between the two fractured pieces upon relaxation of the PTP instrument. As shown in
10 Fig. 3d, a new surface was formed along the edge of the fracture tip. Two types of
11 particles were found: one is the brighter Pt particles deposited on the original sample
12 surface when welding the two ends of the elongated thin foil sample on the PTP chip,
13 and the other type are fine particles which might be shredded β'' precipitates inside the
14 very thin tip. The Pt particles can be further identified by EDX and SAED as shown in
15 Fig. S4, while the fine particles need to be further analyzed through *ex-situ* experiments
16 due to the single α tilt condition of an *in-situ* tensile test (SAED along the $[001]_{Al}$ zone
17 axis is not possible here) and the valley geometry of the Si PTP chip (EDX detection
18 efficiency is low and high resolution elemental mapping is not possible). In addition, it
19 should be noticed that no needle-like β'' precipitate was found in the fracture tip.

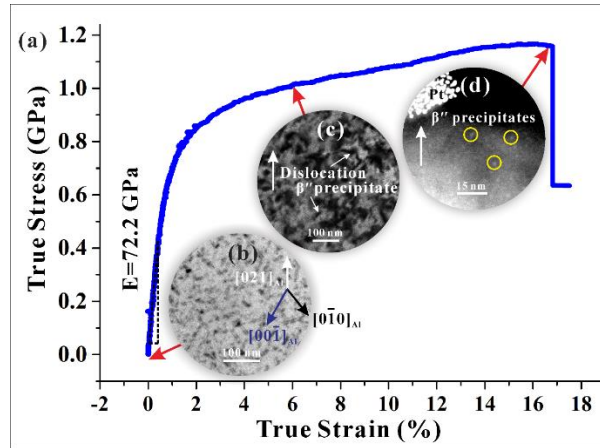


Fig. 3. Nanomechanical and microstructural evolution during the *in-situ* tensile experiment of the sample aged for 3 h. (a) True stress-strain curve, (b-c) BF images before and during the *in-situ* testing, respectively, and (d) HAADF-STEM image of the sample fracture tip after *in-situ* testing. The tensile direction $[021]_{Al}$ is shown by large white arrows.

Details of the interactions between precipitates and dislocations are shown in Fig.

4. A video showing the whole tension process is uploaded as Supplementary Video 1.

The images in Fig. 4 were extracted from the video and processed via ImageJ software

[36] (by removing bright outliers with radius = 2 pixels, threshold = 10, and Gaussian

blurring with sigma/radius = 1.5 pixels, and then applying auto contrast). Five

dislocations (*i*, *ii*, *iii*, *iv* and *v*) and several precipitates are marked by dotted lines and

white circles, respectively. As shown in Fig. 4a, dislocations *i*, *ii*, *iii* and *iv* were

temporarily impeded by precipitates 1, 2, 3 and 4, respectively. Then, with the increase

in tensile stress, these precipitates were sheared by the further gliding of these


previously impeded dislocations, as shown in Fig. 4b. In this step, dislocations *i*, *ii* and

iii were impeded by precipitates 2, 3 and 4, respectively. Immediately after this step,

precipitate 2 was sheared by dislocation *i* (see Fig. 4c), and as a result of further tension,


precipitates 3 and 4 were sheared by dislocations *ii* and *iii* (see Fig. 4d), respectively.

1 In the stage corresponding to Fig. 4d, dislocations *i* and *ii* were hindered by precipitates
 2 3 and 4, respectively. Figs. 4e-4h are the unmarked images of Figs. 4a-4d, respectively,
 3 added for clarity. Obviously, each of the 3 precipitates (2, 3, and 4) was sheared twice
 4 by visible dislocations during the 3.2 s of continuous tension.

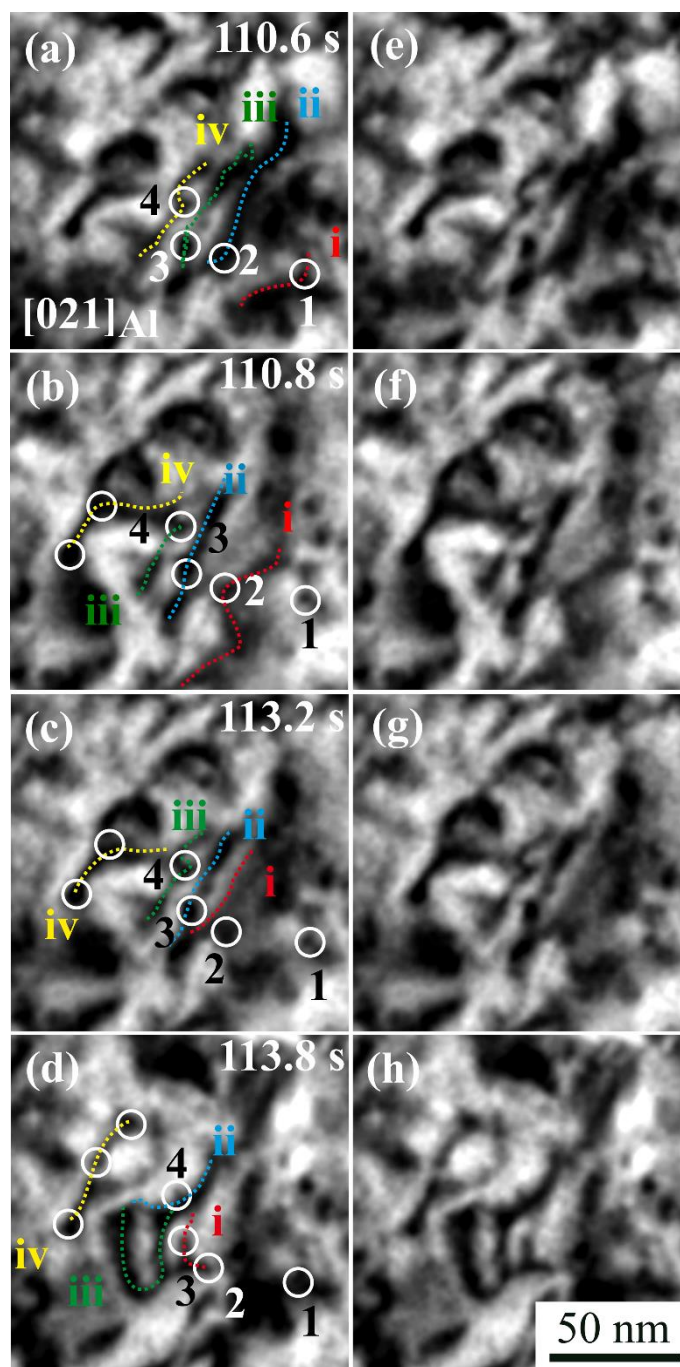

5
 6 **Fig. 4.** *In-situ* BF observation of the interaction between dislocations (colored lines,
 7 Roman numbers) and β'' precipitates (white circles, Arabic numbers) during tension of
 8 the microscale sample (aged for 3 h) at a constant high magnification. (a)-(d) Video

1 frames captured during the *in-situ* tensile deformation under a constant load rate of 0.2
 2 $\mu\text{N/s}$ until the sample breaks. The unmarked images of (a)-(d) are shown in (e)-(h),
 3 respectively.

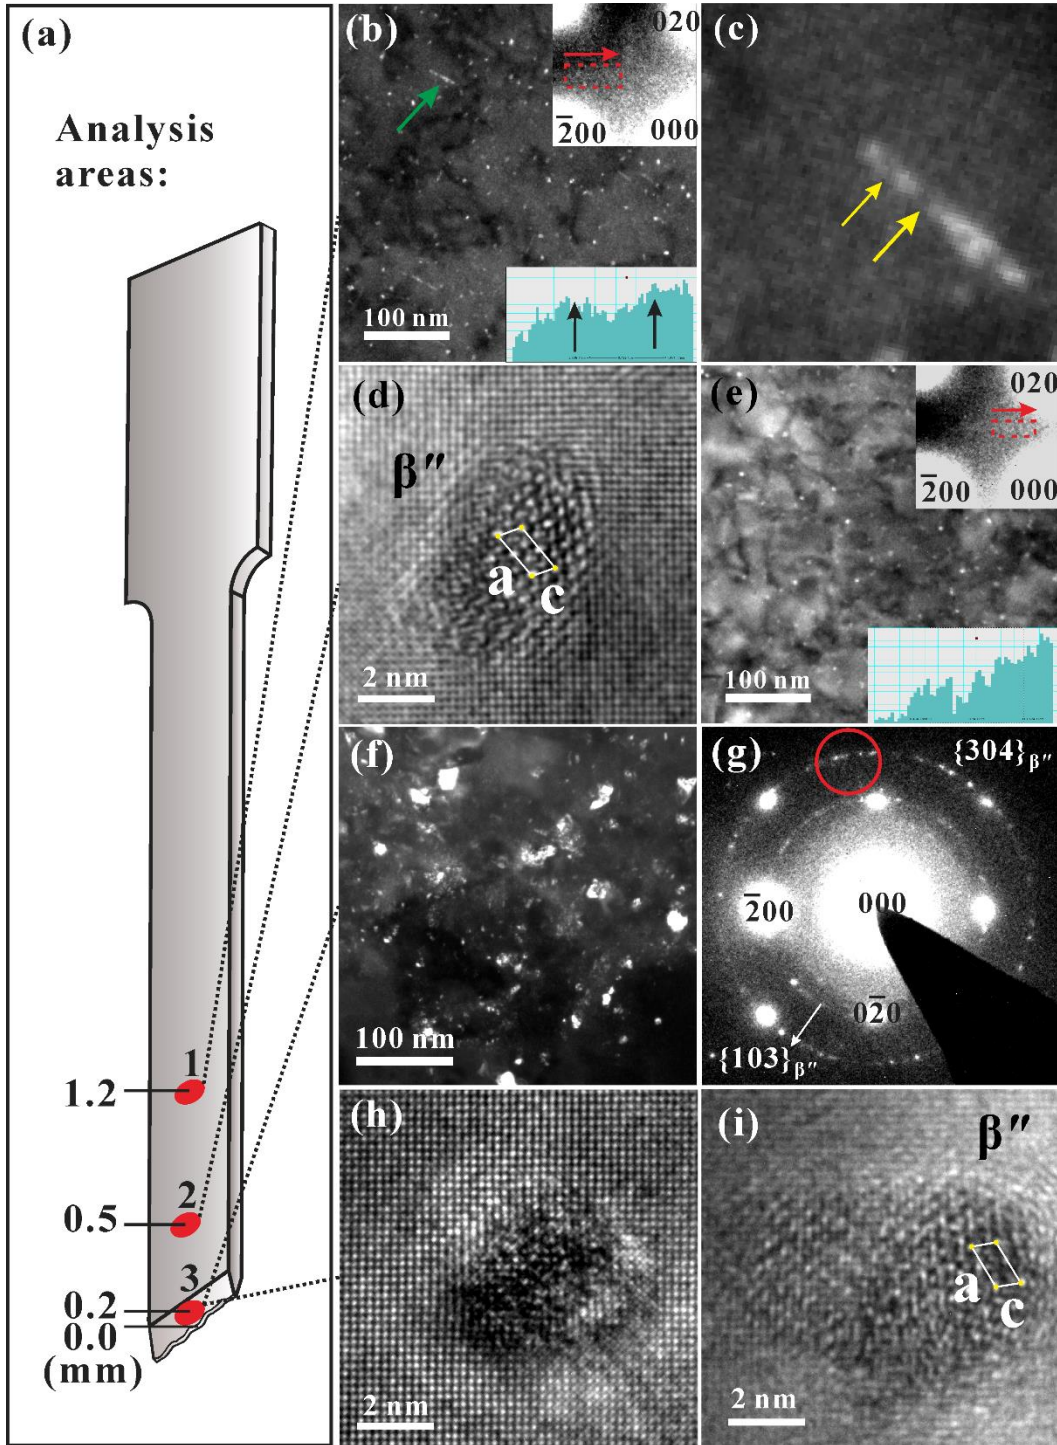

4
 5 **Fig. 5.** *Ex-situ* TEM observation of the areas in (a) a fractured sample after ageing for
 6 3 h and macro tensile test, which are about 1.2 mm (b-d), 0.5 mm (e) and 0.2 mm (f-i)
 7 away from the fracture tip. (b) and (e) dark field images using the diffraction spots
 8 denoted by arrows in the corresponding SAED patterns inserted. **The intensity profiles**
 9 **from the red dotted boxes are also inserted.** In addition, the green arrow in (b) marks a
 10 sheared needle-like β'' precipitate which is shown at a higher magnification in (c). (d)

1 HRTEM image of a β'' precipitate in (b). (f) Dark field image of the fracture tip (only
2 0.2 mm away), and (g) the corresponding SAED pattern. (h) and (i) HRTEM images of
3 two precipitates in the fracture tip. In (h) the observation direction was $[001]_{Al}$ while in
4 (i) it was $[010]_{\beta''}$, which was achieved after further tilting the sample by about 3° from
5 $[001]_{Al}$.
6

7 **3.3 *Ex-situ* TEM evidence for fragmentation and rotation of β'' precipitates during** 8 **deformation**

9 An *ex-situ* TEM sample cut from a fractured specimen after a macro tensile test
10 was electropolished and the area observed in TEM was about 1.2 mm away from the
11 fracture tip (area 1 in Fig. 5a). Needle-like β'' precipitates can be found in the dark field
12 images as shown in Fig. 5b. The precipitate denoted by the green arrow is enlarged in
13 Fig. 5c, showing the trace left by shearing (marked by yellow arrows). The β''
14 precipitate can still be characterized from the HRTEM image in Fig. 5d and the coherent
15 growth direction along $[010]_{\beta''} // [001]_{Al}$ is well maintained. In contrast, in the TEM
16 sample taken from the position about 0.5 mm away from the fracture tip (area 2 in Fig.
17 5a), no needle-like precipitate can be found in the dark field image in Fig. 5e,
18 precipitates were all fragmented due to shearing by dislocations. The cross-shaped
19 diffraction signals from precipitates can still be found in the zoom of the SAED pattern
20 inserted in Fig. 5b, the signal got much weaker for the area shown in Fig. 5e. This is
21 confirmed by the red dotted box scans in Fig. 5b and Fig. 5e where the two peaks are
22 more apparent for Fig. 5b compared to Fig. 5e. These two peaks are the same to those
23 in the red dotted box in Fig. 1b (the undeformed sample), which are more apparent
24 though. This indicates that part of the precipitates in these two samples with some
25 distance from the fracture tip are still maintaining their orientation relationships (ORs)

1 with the Al matrix.

2 In the area very close to the fracture tip (area 3 in Fig. 5a), as shown in Fig. 5f, the
3 precipitates are also fragmented. Besides, there are no visible cross-shaped diffraction
4 spots from precipitates in the SAED pattern in Fig. 5g. It is worth mentioning that
5 polycrystalline diffraction rings of β'' , indexed as $\{103\}_{\beta''}$ and $\{304\}_{\beta''}$, have appeared
6 in the pattern. These rings unambiguously reveal that the β'' precipitates were sheared
7 into small parts and they lost their initial OR with the Al matrix, i.e., they have been
8 rotated. Meanwhile, most precipitates cannot be characterized by HRTEM as typically
9 shown in Fig. 5h, which was obtained exactly along $[001]_{Al}$. In addition, once the zone
10 axis of observation deviates by $\sim 3^\circ$ from $[001]_{Al}$, some pieces of β'' precipitates can be
11 characterized from the HRTEM image as typically shown in Fig. 5i, where the Al lattice
12 fringes are only visible along one direction. The deviation is also seen from the FFT of
13 the Al matrix near the precipitate as shown in Fig. S5.

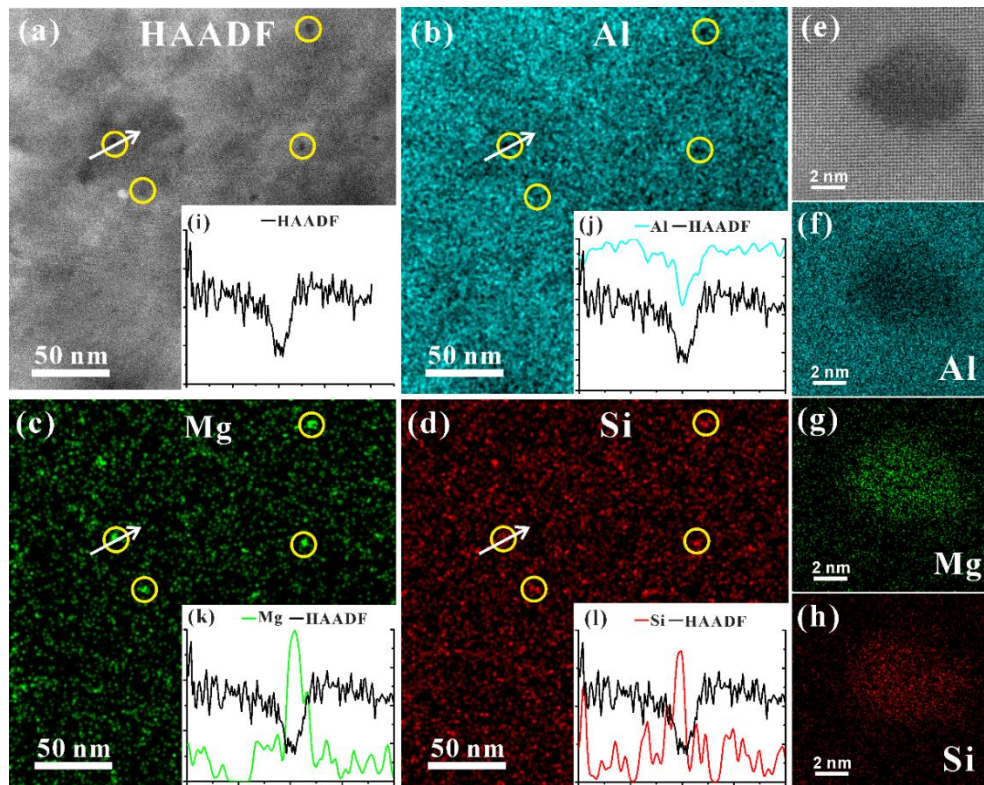


Fig. 6. *Ex-situ* TEM analysis of the fracture tip, corresponding to area 3 in Fig. 5. (a)-(d) and (e)-(h) STEM-EDX results at low and high magnifications, respectively. (i)-(l) Line profiles across a β'' precipitate (indicated by a white arrow, more details are shown in Fig. S6).


The EDX elemental maps of Figs. 6a and 6e are (also from area 3 in Fig. 5a) shown in Figs. 6b-6d and Figs. 6f-6h, respectively. It is seen that the fine particles in Figs. 6a and 6e are rich in Mg and Si. Therefore, these particles are identified as shredded β'' precipitates and they no longer have the needle-like shape.

3.4 Complementary *Ex-situ* TEM and APT studies of sheared β'' and β' precipitates

The TEM results of the area very close to the fracture tip of the sample aged for 2 h were similar to those of the sample aged for 3 h in that only equiaxed shapes (see Fig. 7a) and polycrystalline diffraction rings (see Fig. 7b) of β'' precipitates can be found. Therefore these needle-like precipitates were also sheared into small parts and rotated.

It should be noted that the $\{304\}_{\beta''}$ diffraction rings in Fig. 7b and also in Fig. 5g do not

1 coincide with the $\{220\}_{Al}$ spots, and there is a small shift between them as denoted by
 2 the black cross (indicating the center of the reflection) and the dashed arc in Fig. 7b. On
 3 the contrary, some precipitates (β'' and/or β') in the area very close to the fracture tip of
 4 the sample aged for 6 h were sheared into small parts but their needle-like shape can
 5 still be recognized, while some other precipitates were intact, as shown in Fig. 7c. It
 6 should be noted that both β'' [29] and β' [37], in their characteristic orientations, produce
 7 crossed shaped diffraction spots among Al spots. As the needle-like morphologies of
 8 precipitates can be identified in the dark field image in Fig. 7c using the diffraction
 9 signals in the red circle in Fig. 7d, it is inferred there were indeed β''/β' diffraction
 10 signals but they were too weak to be recorded by the Gatan Model 832 CCD camera
 11 used. Therefore, it is reasonable to speculate that some precipitates still maintain their
 12 original characteristic orientation relationship with the matrix in this tensile-deformed
 13 sample.

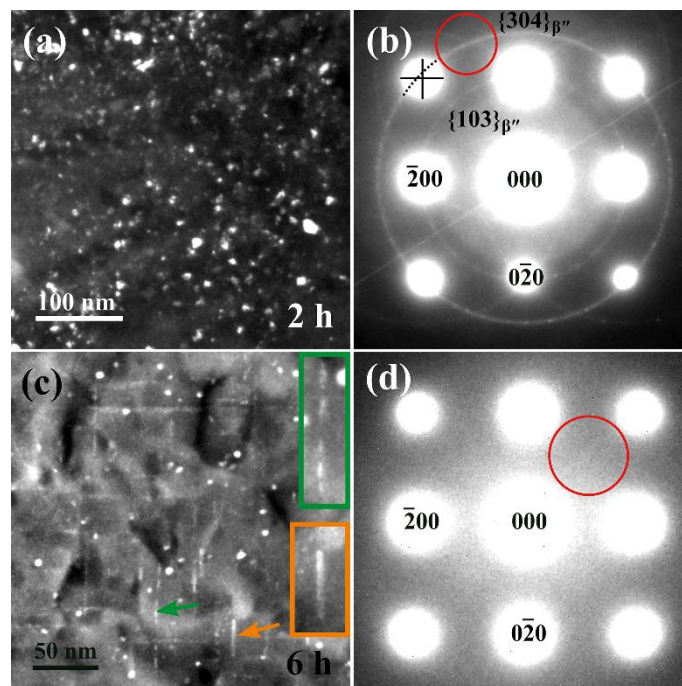


14 **Fig. 7.** *Ex-situ* TEM observations of the areas about 0.2 mm away from the fracture tips
 15

1 of the tensile-tested samples which were aged for 2 h (a-b) and 6 h (c-d). (a) and (c)
 2 Dark-field images, (b) and (d) corresponding SAED patterns. The diffraction signals in
 3 red circles were used for dark field imaging.
 4

5 The frequencies of r_{needle} (equivalent radius of the cross-section) of the needle-like
 6 precipitates, in the undeformed samples aged for 2 h, 3 h and 6 h, are shown in Fig. 8.

7 The values of $r_{\text{needle-2h}}$, $r_{\text{needle-3h}}$, $r_{\text{needle-6h-}\beta''}$ and $r_{\text{needle-6h-}\beta'}$ were measured from 84, 60,
 8 104 and 77 HRTEM images of the precipitates, respectively. It is clear that the
 9 distribution of $r_{\text{needle-6h-}\beta''}$ is completely between the distributions of $r_{\text{needle-2h}}$ and $r_{\text{needle-3h}}$
 10 (for β''). The distribution of $r_{\text{needle-6h-}\beta'}$ resembles that of $r_{\text{needle-6h-}\beta''}$ except 3.9% of β'
 11 precipitates exceed the radius range of β'' precipitates. Since the β'' precipitates were
 12 fragmented and rotated in the areas very close to the fracture tip of the samples aged
 13 for 2 h and 3 h, this should hold true for β'' precipitates with very similar sizes in the
 14 similarly treated sample aged for 6 h. Therefore, it is inferred that the precipitates
 15 retaining a needle-like shape in the deformed sample aged for 6 h are β' .

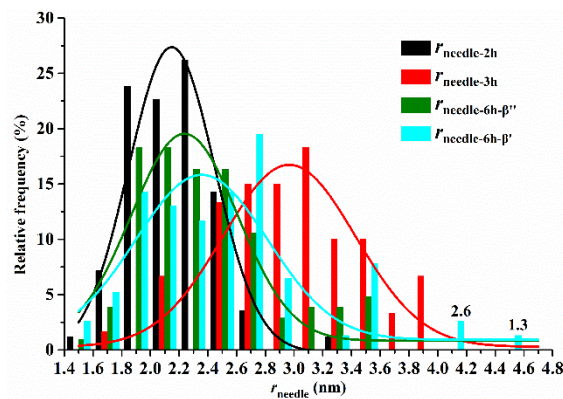


16
 17 **Fig. 8.** The distribution of r_{needle} of the precipitates in the undeformed samples aged for
 18 different times. The histogram shows the frequency counts of $r_{\text{needle-2h}}$ (in black), $r_{\text{needle-3h}}$
 19 (in red), $r_{\text{needle-6h-}\beta''}$ (in green) and $r_{\text{needle-6h-}\beta'}$ (in blue) with corresponding Gaussian
 20 fitting curves.
 21

22 APT characterization of a tip specimen made close to the fracture surface of a
 23 tensile-tested sample aged for 6 h are shown in Fig. 9. The analyzed volume contains

1 precipitates with various sizes and morphologies including needles, short needles and
2 equiaxed particles. It is known that the typical β'' - $\text{Mg}_5\text{Al}_2\text{Si}_4$ precipitate has a Mg/Si
3 ratio of 1.25 [38], smaller than 1.8 of the β' - Mg_9Si_5 precipitate [39]. Our TEM
4 characterization of the sample under the same aging condition (but undeformed)
5 confirmed that the $V_{f-6h-\beta''}/V_{f-6h-\beta'}$ ratio is 0.68/0.57 [30]. In order to differentiate
6 precipitates observed in the APT analyzed volume, particles with Mg/Si ratios smaller
7 than 1.9 were considered to be β'' , the others with higher Mg/Si ratios are considered to
8 be β' . Interestingly, the volume fraction ratio of the two groups of precipitates was found
9 to be 0.64/0.57, close to 0.68/0.57 measured by TEM. Both the average Mg/Si ratios
10 (the dashed lines in Figs. 9b and 9c) of the two groups of precipitates detected by APT
11 are a little higher than the standard Mg/Si ratios of β'' and β' precipitates by 0.25~0.35.
12 This is largely due to some small fragments of β' detected with low Mg/Si ratios failed
13 to be picked out correctly by our method. Wrong classification of them into β'' group
14 would push the average Mg/Si ratio higher as a result. Such difficulty in APT
15 measurement is mainly due to that the detection efficiency is only about 55% for LEAP
16 4000X SI and large scattering in Mg/Si ratios of small features detected is expected. It
17 is important to notice that most of (20/23, i.e. 87%) of the particles smaller than 200
18 nm^3 are β'' precipitates, and 8 of them with individual volumes less than 30 nm^3 .
19 Combined with our previous work that the smallest volume of precipitates is 68.1 nm^3
20 in the undeformed sample under the same aging condition [30], one can deduce that the
21 particles with sizes less than 30 nm^3 which are inside the analyzed volume (not cut by
22 the surface of the analyzed volume) are broken pieces of β'' precipitates (see the light

1 green ellipse mark in Fig. 9c). In another word, the current APT results confirm that β''
 2 precipitates are much easier than β' precipitates to be sheared into small pieces by
 3 gliding dislocations during tensile deformation.

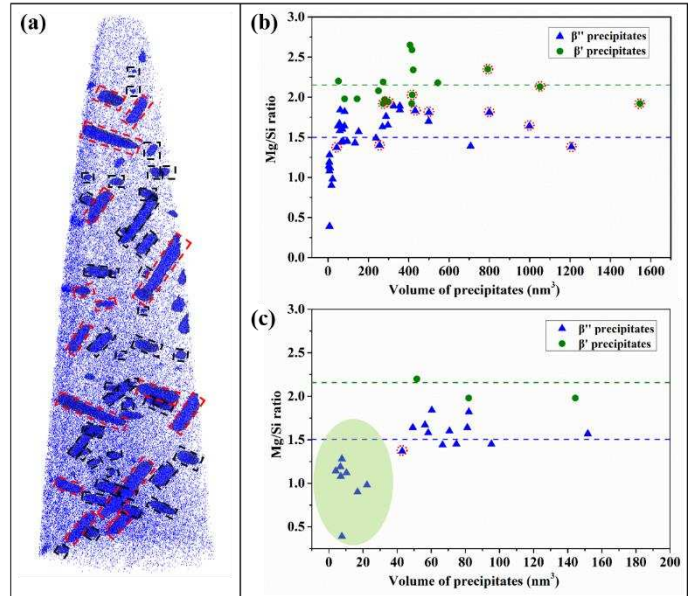

4
 5 **Fig. 9.** APT studies of precipitates in an area about 2.3 mm away from the fracture tip
 6 of the tensile-deformed sample aged for 6 h. (a) A reconstructed volume of
 7 $90 \times 90 \times 286 \text{ nm}^3$ with precipitates, which are visualized by adding iso-composition
 8 surfaces of 3.0 at.% Si. (b) The Mg/Si ratio vs the volume of each β'' or β' precipitate,
 9 over 53 precipitates in total. (c) Mg/Si ratio vs volume of each small β'' and β'
 10 precipitate (over 23 precipitates) with its volume less than 200 nm^3 . The precipitates
 11 marked with black dotted rectangles are in the APT needle tip sample, those marked
 12 with red dotted rectangles are not completely embedded in the current tip. The data
 13 points marked with red dotted circles in (b-c) correspond to the precipitates marked
 14 with red dotted rectangles in (a).

15 **4. Discussion**

16 **4.1 The shearable nature of the β'' precipitate in its size range**

17 The face-centered cubic (fcc) Al matrix has 12 slip systems consisting of $\{111\}$ slip
 18 planes and $\langle 110 \rangle$ slip directions [40]. When the resolved shear stress of a slip system
 19 is greater than its critically resolved shear stress, dislocations will start to slip on the
 20 slip systems during deformation [41]. These moving dislocations will shear the β''

1 precipitates in Al-Mg-Si alloys, and cross slip will occur among screw dislocations [14].
2
3 With increasing the level of deformation, the segments of precipitates were
4
5 continuously being sheared. In this work it has been verified that β'' precipitates are
6
7 shearable, and the critical precipitate radius for the transition from shearable to non-
8
9 shearable interactions is found larger than 6.75 nm or 4.0 nm in the sphere model or the
10
11 needle model, respectively. Our results thus strongly imply that β'' should be considered
12
13 as shearable when modelling mechanical properties, since the β'' precipitates observed
14
15 here are the largest that one can find in the literature [8, 13, 14, 20]. Our findings support
16
17 previous investigations in which β'' precipitates were found to grow and coarsen but
18
19 remain shearable when aging proceeds [13, 14]. The details of the shearing mechanism
20
21 of β'' precipitates can be found in Ref. [25].
22
23

24 **4.2 Mechanisms lying behind different shearing and rotation behaviors between** 25 **β'' and β' precipitates** 26

27 It is reported that dislocations shearing weakens coherent precipitates but
28
29 strengthens semi-coherent precipitates [9]. The resistance of a coherent precipitate to
30
31 secondary shear is reduced after the principle shear of the precipitate [42, 43]. Thus,
32
33 dislocations can shear multiple times at the same location in a coherent precipitate, but
34
35 this is quite difficult for semi-coherent precipitates because the new interfaces caused
36
37 by dislocation shearing are with large misfit. As a result, a higher slip localization can
38
39 be achieved in alloys strengthened by coherent precipitates than in alloys strengthened
40
41 by semi-coherent precipitates [9, 44]. The coherent β'' precipitates are thus fragmented
42
43 as displayed in Figs. 10a-10b, and the corresponding mechanism is schematically
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

shown in Figs. 10d-10g.

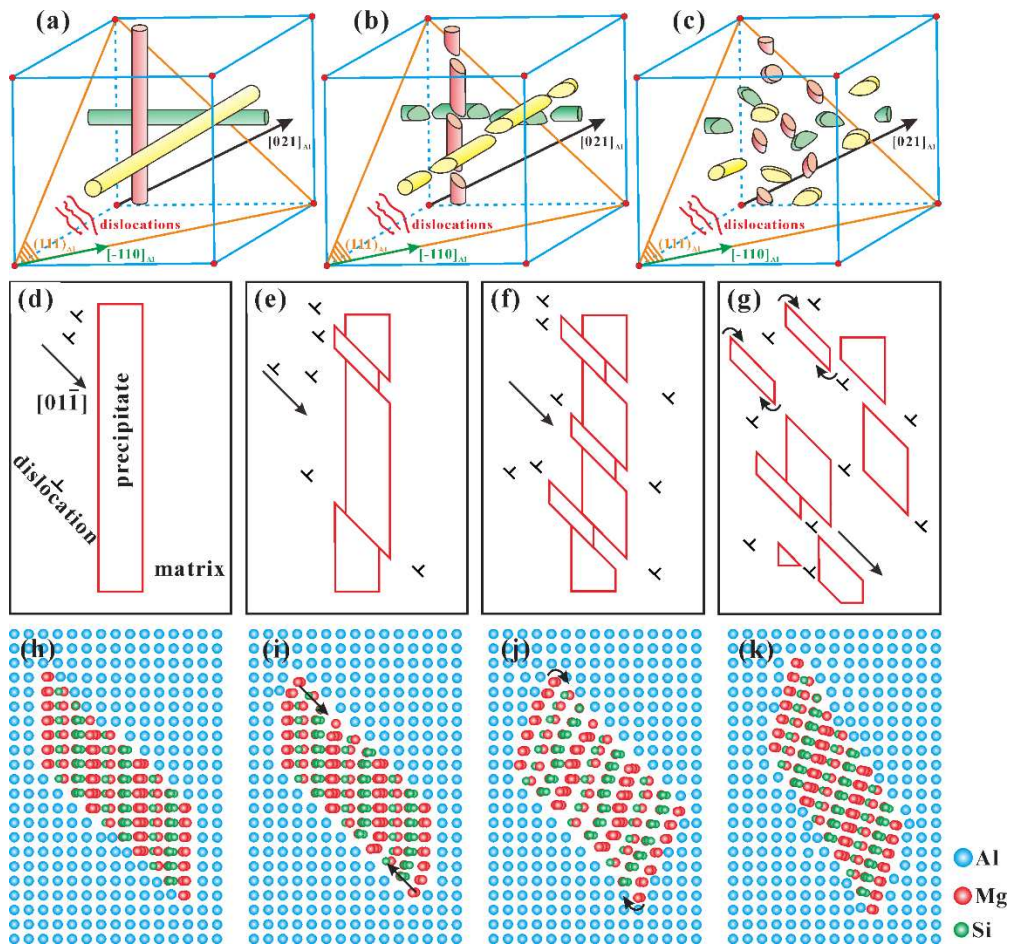


Fig. 10. Schematic diagram of the consequences of the interaction between precipitates and dislocations. (a) Precipitates before the interaction with dislocations. (b) Precipitates are sheared by dislocations. (c) Precipitates are further shredded into small parts which lose the initial ORs with the Al matrix. The mechanism of precipitates being sheared by dislocations is shown in (d) - (h). Black arrows represent gliding of dislocations along $[01\bar{1}]_{Al}$. (i) - (l) The proposed mechanism for rotation of (small parts of) precipitates by GB sliding mediated by diffusion. Large angles are used here to visualize the rotations.

In contrast, in the case of our work, slip localization of semi-coherent β' precipitates was found to be difficult, and most of them cannot be fragmented under the similar deformation which breaks apart coherent β'' precipitates. A more severely mismatched

1 interface and a step with stronger strain field around it will be created after the less
2 coherent β' is being sheared by dislocations. The highly strained interface then becomes
3 a high energy boundary, which is not energetically favorable [9]. As a result, the rotation
4 mechanism through slip localization, as proposed by Guétaz and Pénisson [23], can
5 hardly be activated for β' precipitates in this work. This can explain why β' precipitates
6 can basically maintain the original OR with the Al matrix and mostly keep in needle-
7 like shape, while β'' precipitates were fragmented and rotated during similar tensile
8 deformation processes.

9 **4.3 The rotation mechanism of fragmented β'' precipitates**

10 The recent SPED work of Christiansen et al. [24, 25] on sheared β'' precipitates in
11 an 20% compressed Al-Mg-Si alloy revealed that the precipitates are fragmented into
12 small parts while the original needle-like shape can still be recognized, this is a state
13 very close to that shown in Figs. 5b-5c. They proved the non-existence of rotation of
14 these parts compared to the original OR at this stage, as diffraction spots of these parts
15 are still within the cross-shaped diffraction characteristics of unsheared β'' precipitates.
16 It is thus inferred that the rotation of discrete β'' precipitate parts observed in this work
17 occurred in a deformation condition more severe than in their work. In other words,
18 further shearing are required to rotate the just-fragmented β'' precipitates. Thus, the
19 rotation mechanism during fragmentation of semi-coherent precipitates through
20 multiple shears, as discovered by Guétaz and Pénisson [23], cannot explain the rotation
21 of coherent β'' precipitates observed in this work.

22 At the atomic scale, there are mainly 3 mechanisms leading to grain rotation, i.e.

1 (1) climb of grain boundary (GB) dislocations towards triple-joint (TJ) points [45] and
2 free surfaces, (2) cross-grain glide of dislocations [46], and (3) GB sliding through
3 diffusional processes [47-49]. The first mechanism is not possible in our *ex-situ*
4 experiments because in a large Al grain (~ 80 μm) with nano-precipitates embedded
5 inside, the TJ points and the free surfaces of the millimeter-scale sample are too far
6 away from a dislocation at a precipitate/matrix boundary. The second mechanism
7 through cross-grain glide of dislocations has already been denied by the findings of
8 Christiansen et al. [24, 25], it indeed occurred (from the matrix to the precipitate and
9 then to the matrix) and caused the fragmentation of β'' precipitates, but there was no
10 rotation, probably due to the coherent nature of the interface structures. GB sliding can
11 occur because diffusion is very active during deformation of aluminum even at room
12 temperature. For instance, in the work of Hutchinson et al. [50], vacancies were injected
13 into cyclically deformed solution-heat-treated Al alloys at room temperature, and
14 precipitates were formed without a real aging process. Besides, the heterophase
15 boundaries existing in this work are more preferable for sliding than homophase
16 boundaries [51]. Furthermore, a more recent work reported rise of temperature to 1250-
17 2450°C in the shear band during quasi-static loading of a titanium alloy at room
18 temperature [52]. Traces of shear bands were also found in the current alloy (see Figs.
19 S7 and S8 in the Supplementary Document), deformed either *in-situ* or *ex-situ*. In the
20 current aluminum alloy with a relatively low melting point around 650°C, a slight rise
21 in temperature can notably increase the probability of diffusion and GB sliding,
22 resulting in the rotation of precipitate parts. The rotation process of the coherent β''

1 precipitate parts is shown in the schematics of Figs. 10b-10c and explained in Figs. 10h-
2 10k. In the current stage, the precipitate parts are speculated to rotate a very small angle
3 each time and rotation accumulates step by step to a large angle. Our discovery of the
4 rotation of coherent fine nano-precipitates in a plastic Al matrix during deformation
5 expands our knowledge on the alloy's deformation. However, future *in-situ* analysis of
6 the rotation mechanism at the atomic scale remains worthwhile.

8 **5. Conclusions**

9 The interaction between β'' precipitates and dislocations during tensile deformation
10 of an Al-Mg-Si alloy was systematically investigated by the *in-situ* and *ex-situ* TEM
11 observations as well as APT studies, and placed in comparison to that of β' precipitates.
12 These two types of precipitates showed different shearing and rotation behaviors, and
13 the interaction mechanisms were discussed. Detailed findings are as follows:

14 (1) β'' nano-precipitates can be sheared into fragments by gliding dislocations
15 during deformation. The β'' precipitates, which are observed in this work, with
16 needle radius as large as 4 nm, were all found sheared and no intact precipitate
17 could be found. As these are almost the largest β'' precipitates found in the
18 literature, it is inferred that all β'' precipitates are shearable. In the just-
19 fragmented state, the β'' fragments maintain their original OR with the matrix.

20 (2) With continuous increase of deformation and the corresponding increase in
21 number of shearing dislocations, coherent β'' precipitates were further sheared
22 into fine discrete equiaxed particles and rotated, until the sample fractured. As

1 a result, their initial OR with the matrix changed. This is probably mediated via
2 the precipitate/matrix boundary sliding facilitated by diffusion, a different
3 mechanism from that proposed previously for semi-coherent precipitates
4 through slip localization.

5 (3) The semi-coherent β' precipitates can also be sheared by dislocations but the
6 probability was much lower than that of β'' . They can basically maintain the
7 needle-like shape and their original OR with the matrix. This is mainly due to
8 the fact that the interfaces with higher energies, which is formed after the less
9 coherent β' precipitates being sheared by dislocations, is not energetically
10 favorable compared to those of β'' precipitates. Slip localization is more
11 difficult for β' precipitates and thus almost no subsequent rotation can happen.

14 **Supplementary Data**

15 Supplementary data are available online.

17 **Acknowledgement**

18 This work was financially supported by the National Natural Science Foundation of
19 China (52071340, 51711530713 and 51820105001), the Flemish Science Foundation
20 (FWO; VS.026.18N) and the Fundamental Research Funds for the Central Universities
21 (WUT: 2019III012GX, 2020III002GX). The authors thank the EMAT lab at UA, the
22 Center for Materials Research and Analysis and the State Key Laboratory of Silicate

1 Materials for Architectures at WUT, as well as the Advanced Research Center at CSU
2 for use of TEMs.

3 4 **Author contributions**

5 M.J.Y. and A.O. contributed equally to this work. K.L., Y.D. and D.S. designed the
6 project and guided the research. M.J.Y. conducted the *ex-situ* TEM experiments. A.O.
7 and V.S. conducted the *in-situ* TEM experiments with M.J.Y. and K.L.. Z.Y.H.
8 conducted STEM-EDX experiments. M. F. and S.B.J conducted APT experiment.
9 M.J.Y. and A.O. wrote the initial draft. K.L., M.S., G.S., Y.D., G.V.T. and D.S. finalised
10 the paper. All authors contributed to extensive discussions of the results.

11 12 **Competing interests**

13 The authors declare no competing interests.

14 15 **References**

- 16 [1] C. Puncreobutr, A. B. Phillion, J. L. Fife, P. Rockett, A. P. Horsfield, P. D. Lee. In situ quantification of
17 the nucleation and growth of Fe-rich intermetallics during Al alloy solidification, *Acta Mater.* 79 (2014)
18 292-303.
- 19 [2] Edwards GA, Stiller K, Dunlop GL, C. MJ. The precipitation Sequence in Al-MgSi Alloys, *Acta Mater.*
20 46 (1998) 3893-3904.
- 21 [3] C. D. Marioara, H. Nordmark, S. J. Andersen, R. Holmestad. Post- β'' phases and their influence on
22 microstructure and hardness in 6xxx Al-Mg-Si alloys, *J. Mater. Sci.* 41 (2006) 471-478.
- 23 [4] H. W. Zandbergen, S. J. Andersen, J. Jansen. Structure determination of Mg₅Si₆ particles in Al by
24 dynamic electron diffraction studies, *Science.* 277 (1997) 1221.
- 25 [5] L. Ding, Z. Jia, J. F. Nie, Y. Weng, L. Cao, H. Chen, X. Wu, Q. Liu. The structural and compositional
26 evolution of precipitates in Al-Mg-Si-Cu alloy, *Acta Mater.* 145 (2018) 437-450.
- 27 [6] S. Wenner, R. Holmestad. Accurately measured precipitate–matrix misfit in an Al–Mg–Si alloy by
28 electron microscopy, *Scr. Mater.* 118 (2016) 5-8.
- 29 [7] K. Teichmann, C. D. Marioara, S. J. Andersen, K. Marthinsen. TEM study of β' precipitate interaction

1 mechanisms with dislocations and β' interfaces with the aluminium matrix in Al–Mg–Si alloys, Mater.
2 Charact. 75 (2013) 1-7.

3 [8] M. Vivas, P. Lours, C. Levaillant, A. Couret, M. J. Casanove, A. Coujou. Determination of precipitate
4 strength in aluminium alloy 6056-T6 from transmission electron microscopy in situ straining data, Philos.
5 Mag. A. 76 (1997) 921-931.

6 [9] B. Q. Li, F. E. Wawner. Dislocation interaction with semicoherent precipitates (Ω phase) in deformed
7 Al–Cu–Mg–Ag alloy, Acta Mater. 46 (1998) 5483-5490.

8 [10] F. Delmas, J. Majimel, M. Vivas, G. Molenat, A. Couret, A. Coujou. Cross-slip and glide in {001}
9 planes of Al–Mg–Si alloy 6056, Philos. Mag. Lett. 83 (2003) 289-296.

10 [11] F. Delmas, M. Vivas, P. Lours, M. J. Casanove, A. Couret, A. Coujou. Straining mechanisms in
11 aluminium alloy 6056. In-situ investigation by transmission electron microscopy, Mater. Sci. Eng. A. 340
12 (2003) 286-291.

13 [12] P. Donnadiou, G. F. Dirras, J. Douin. An approach of precipitate/dislocation interaction in age-
14 hardened Al–Mg–Si Alloys: measurement of the strain field around precipitates and related simulation
15 of the dislocation propagation, Mater. Sci. Forum. 396-402 (2002) 1019-1024.

16 [13] W. J. Poole, X. Wang, D. J. Lloyd, J. D. Embury. The shearable–non-shearable transition in Al–Mg–
17 Si–Cu precipitation hardening alloys: implications on the distribution of slip, work hardening and
18 fracture, Philos. Mag. 85 (2005) 3113-3135.

19 [14] K. Misumi, K. Kaneko, T. Nishiyama, T. Maeda, K. Yamada, K.-i. Ikeda, M. Kikuchi, K. Takata, M. Saga,
20 K. Ushioda. Three-dimensional characterization of interaction between β'' precipitate and dislocation in
21 Al–Mg–Si alloy, J. Alloy. Compd. 600 (2014) 29-33.

22 [15] T. Saito, C. D. Marioara, S. J. Andersen, W. Lefebvre, R. Holmestad. Aberration-corrected HAADF-
23 STEM investigations of precipitate structures in Al–Mg–Si alloys with low Cu additions, Philos. Mag. 94
24 (2013) 520-531.

25 [16] E. Hornbogen, E. A. S. Jr. Overview no. 102 Theory assisted design of high strength low alloy
26 aluminum, Acta Metall. Mater. 41 (1993) 1-16.

27 [17] L. Proville, B. Bakó. Dislocation depinning from ordered nanophases in a model fcc crystal: From
28 cutting mechanism to Orowan looping, Acta Mater. 58 (2010) 5565-5571.

29 [18] S. Esmaeili, D. J. Lloyd, W. J. Poole. A yield strength model for the Al–Mg–Si–Cu alloy AA6111, Acta
30 Mater. 51 (2003) 2243-2257.

31 [19] O. R. Myhr, Ø. Grong, S. J. Andersen. Modelling of the age hardening behaviour of Al–Mg–Si alloys,
32 Acta Materialia. 49 (2001) 65-75.

33 [20] X. Wang, J. D. Embury, W. J. Poole, S. Esmaeili, D. J. Lloyd. Precipitation strengthening of the
34 aluminum alloy AA6111, Metall. Mater. Trans. A. 34 (2003) 2913-2924.

35 [21] C. Xu, M. Furukawa, Z. Horita, T. G. Langdon. Using ECAP to achieve grain refinement, precipitate
36 fragmentation and high strain rate superplasticity in a spray-cast aluminum alloy, Acta Mater. 51 (2003)
37 6139-6149.

38 [22] M. Murayama, Z. Horita, K. Hono. Microstructure of two-phase Al–1.7 at% Cu alloy deformed by
39 equal-channel angular pressing, Acta Mater. 49 (2001) 21-29.

40 [23] L. Guétaz, J. Pénisson. High resolution electron microscopy of a deformed superalloy: shear of
41 precipitates, Mater. Sci. Eng. A. 175 (1994) 141-148.

42 [24] E. Christiansen, C. D. Marioara, B. Holmedal, O. S. Hopperstad, R. Holmestad. Nano-scale
43 characterisation of sheared β'' precipitates in a deformed Al–Mg–Si alloy, Scientific Reports. 9 (2019)
44 17446.

- 1 [25] E. Christiansen, C. D. Marioara, I. G. Ringdalen, R. Bjørge, B. Holmedal, O. S. Hopperstad, R.
2 Holmestad, A. Deschamps, J. C. Ehrström, P. Jarry, G. Salloum-Abou-Jaoude, L. Salvo, C. Sigli. Detailed
3 investigation of the shearing mechanism of β'' precipitates in Al-Mg-Si alloys, MATEC Web of
4 Conferences. 326 (2020) 01005.
- 5 [26] V. Samaeeaghmiyoni, H. Idrissi, J. Groten, R. Schwaiger, D. Schryvers. Quantitative in-situ TEM
6 nanotensile testing of single crystal Ni facilitated by a new sample preparation approach, Micron. 94
7 (2017) 66-73.
- 8 [27] K. Li, H. Idrissi, G. Sha, M. Song, J. Lu, H. Shi, W. Wang, S. P. Ringer, Y. Du, D. Schryvers. Quantitative
9 measurement for the microstructural parameters of nano-precipitates in Al-Mg-Si-Cu alloys, Mater.
10 Charact. 118 (2016) 352-362.
- 11 [28] D. J. Larson, T. J. Prosa, R. M. Ulfig, B. P. Geiser, T. F. Kelly. Specimen Preparation. In: Larson DJ, Prosa
12 TJ, Ulfig RM, Geiser BP, Kelly TF, editors. Local Electrode Atom Probe Tomography: A User's Guide. New
13 York, NY: Springer New York, 2013. p.25-53.
- 14 [29] K. Li, M. Song, Y. Du, H. Zhang. Simulation of the electron diffraction patterns from needle/rod-like
15 precipitates in Al-Mg-Si alloys, Mater. Charact. 62 (2011) 894-903.
- 16 [30] M. Yang, H. Chen, A. Orekhov, Q. Lu, X. Lan, K. Li, S. Zhang, M. Song, Y. Kong, D. Schryvers, Y. Du.
17 Quantified contribution of β'' and β' precipitates to the strengthening of an aged Al-Mg-Si alloy, Mater.
18 Sci. Eng. A. 774 (2020) 138776.
- 19 [31] H. Idrissi, A. Kobler, B. Amin-Ahmadi, M. Coulombier, M. Galceran, J.-P. Raskin, S. Godet, C. Kübel,
20 T. Pardoen, D. Schryvers. Plasticity mechanisms in ultrafine grained freestanding aluminum thin films
21 revealed by in-situ transmission electron microscopy nanomechanical testing, Appl. Phys. Lett. 104
22 (2014) 101903.
- 23 [32] C. Zhou, I. J. Beyerlein, R. LeSar. Plastic deformation mechanisms of fcc single crystals at small
24 scales, Acta Mater. 59 (2011) 7673-7682.
- 25 [33] Y. Xiang, J. J. Vlassak. Bauschinger and size effects in thin-film plasticity, Acta Mater. 54 (2006) 5449-
26 5460.
- 27 [34] M. Yaghoobi, G. Z. Voyiadjis. Size effects in fcc crystals during the high rate compression test, Acta
28 Mater. 121 (2016) 190-201.
- 29 [35] W. Xu, L. P. Dávila. Size dependence of elastic mechanical properties of nanocrystalline aluminum,
30 Mater. Sci. Eng. A. 692 (2017) 90-94.
- 31 [36] C. A. Schneider, W. S. Rasband, K. W. Eliceiri. NIH Image to ImageJ: 25 years of image analysis, Nat
32 Methods. 9 (2012) 671-675.
- 33 [37] W. Yang, M. Wang, X. Sheng, Q. Zhang, L. Huang. Precipitate characteristics and selected area
34 diffraction patterns of the β' and Q' precipitates in Al-Mg-Si-Cu alloys, Philos. Mag. Lett. 91 (2011) 150-
35 160.
- 36 [38] S. Wenner, L. Jones, C. D. Marioara, R. Holmestad. Atomic-resolution chemical mapping of ordered
37 precipitates in Al alloys using energy-dispersive X-ray spectroscopy, Micron. 96 (2017) 103-111.
- 38 [39] R. Vissers, M. A. van Huis, J. Jansen, H. W. Zandbergen, C. D. Marioara, S. J. Andersen. The crystal
39 structure of the β' phase in Al-Mg-Si alloys, Acta Mater. 55 (2007) 3815-3823.
- 40 [40] A. G. Jackson. Slip systems. In: Jackson AG, editor. Handbook of Crystallography: For Electron
41 Microscopists and Others. New York, NY: Springer New York, 1991. p.83-88.
- 42 [41] G. Gottstein. Physical foundations of materials science: Springer Science & Business Media, 2013.
- 43 [42] T. H. Sanders, E. A. Starke. The effect of slip distribution on the monotonic and cyclic ductility of
44 Al-Li binary alloys, Acta Metall. 30 (1982) 927-939.

1 [43] E. Hornbogen, K. H. Zum Gahr. Distribution of plastic strain in alloys containing small particles,
2 Metallography. 8 (1975) 181-202.

3 [44] B. Zhang, L. Wu, B. Wan, J. Zhang, Z. Li, H. Gou. Structural evolution, mechanical properties, and
4 electronic structure of Al–Mg–Si compounds from first principles, J. Mater. Sci. 50 (2015) 6498-6509.

5 [45] L. Wang, J. Teng, P. Liu, A. Hirata, E. Ma, Z. Zhang, M. Chen, X. Han. Grain rotation mediated by
6 grain boundary dislocations in nanocrystalline platinum, Nat. Commun. 5 (2014) 4402.

7 [46] V. Yamakov, D. Wolf, S. R. Phillpot, A. K. Mukherjee, H. Gleiter. Deformation-mechanism map for
8 nanocrystalline metals by molecular-dynamics simulation, Nat. Mater. 3 (2004) 43-47.

9 [47] I. A. Ovid'ko, A. G. Sheinerman. Special rotational deformation in nanocrystalline metals and
10 ceramics, Scr. Mater. 59 (2008) 119-122.

11 [48] J. W. Cahn, J. E. Taylor. A unified approach to motion of grain boundaries, relative tangential
12 translation along grain boundaries, and grain rotation, Acta Mater. 52 (2004) 4887-4898.


13 [49] D. Moldovan, D. Wolf, S. R. Phillpot. Theory of diffusion-accommodated grain rotation in columnar
14 polycrystalline microstructures, Acta Mater. 49 (2001) 3521-3532.


15 [50] W. Sun, Y. Zhu, R. Marceau, L. Wang, Q. Zhang, X. Gao, C. Hutchinson. Precipitation strengthening
16 of aluminum alloys by room-temperature cyclic plasticity, Science. 363 (2019) 972.


17 [51] M. E. Kassner. Fundamentals of creep in metals and alloys: Butterworth-Heinemann, 2015.


18 [52] L. Choisez, L. Ding, M. Marteleur, H. Idrissi, T. Pardoen, P. J. Jacques. High temperature rise
19 dominated cracking mechanisms in ultra-ductile and tough titanium alloy, Nat. Commun. 11 (2020).


20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

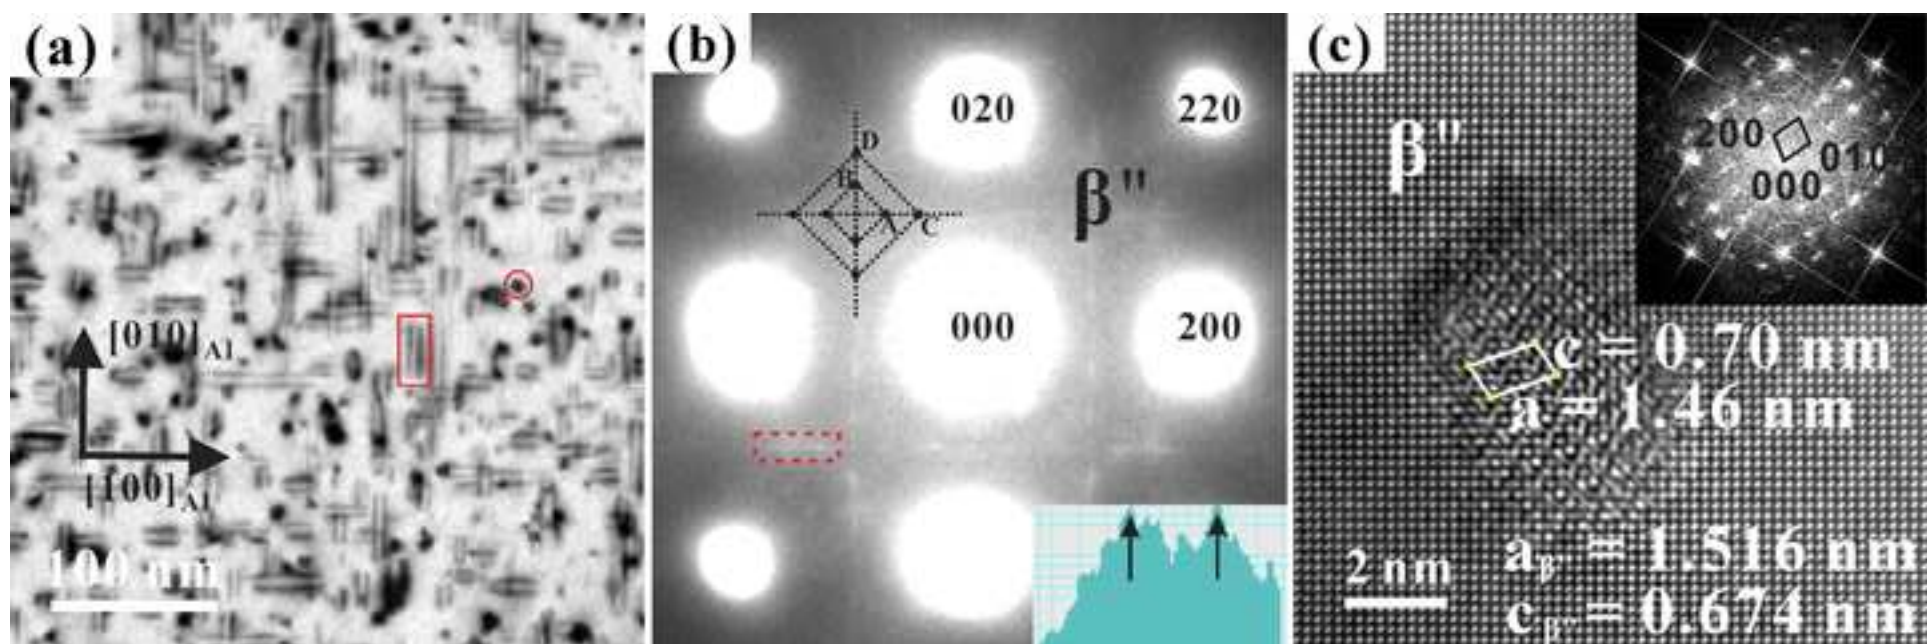


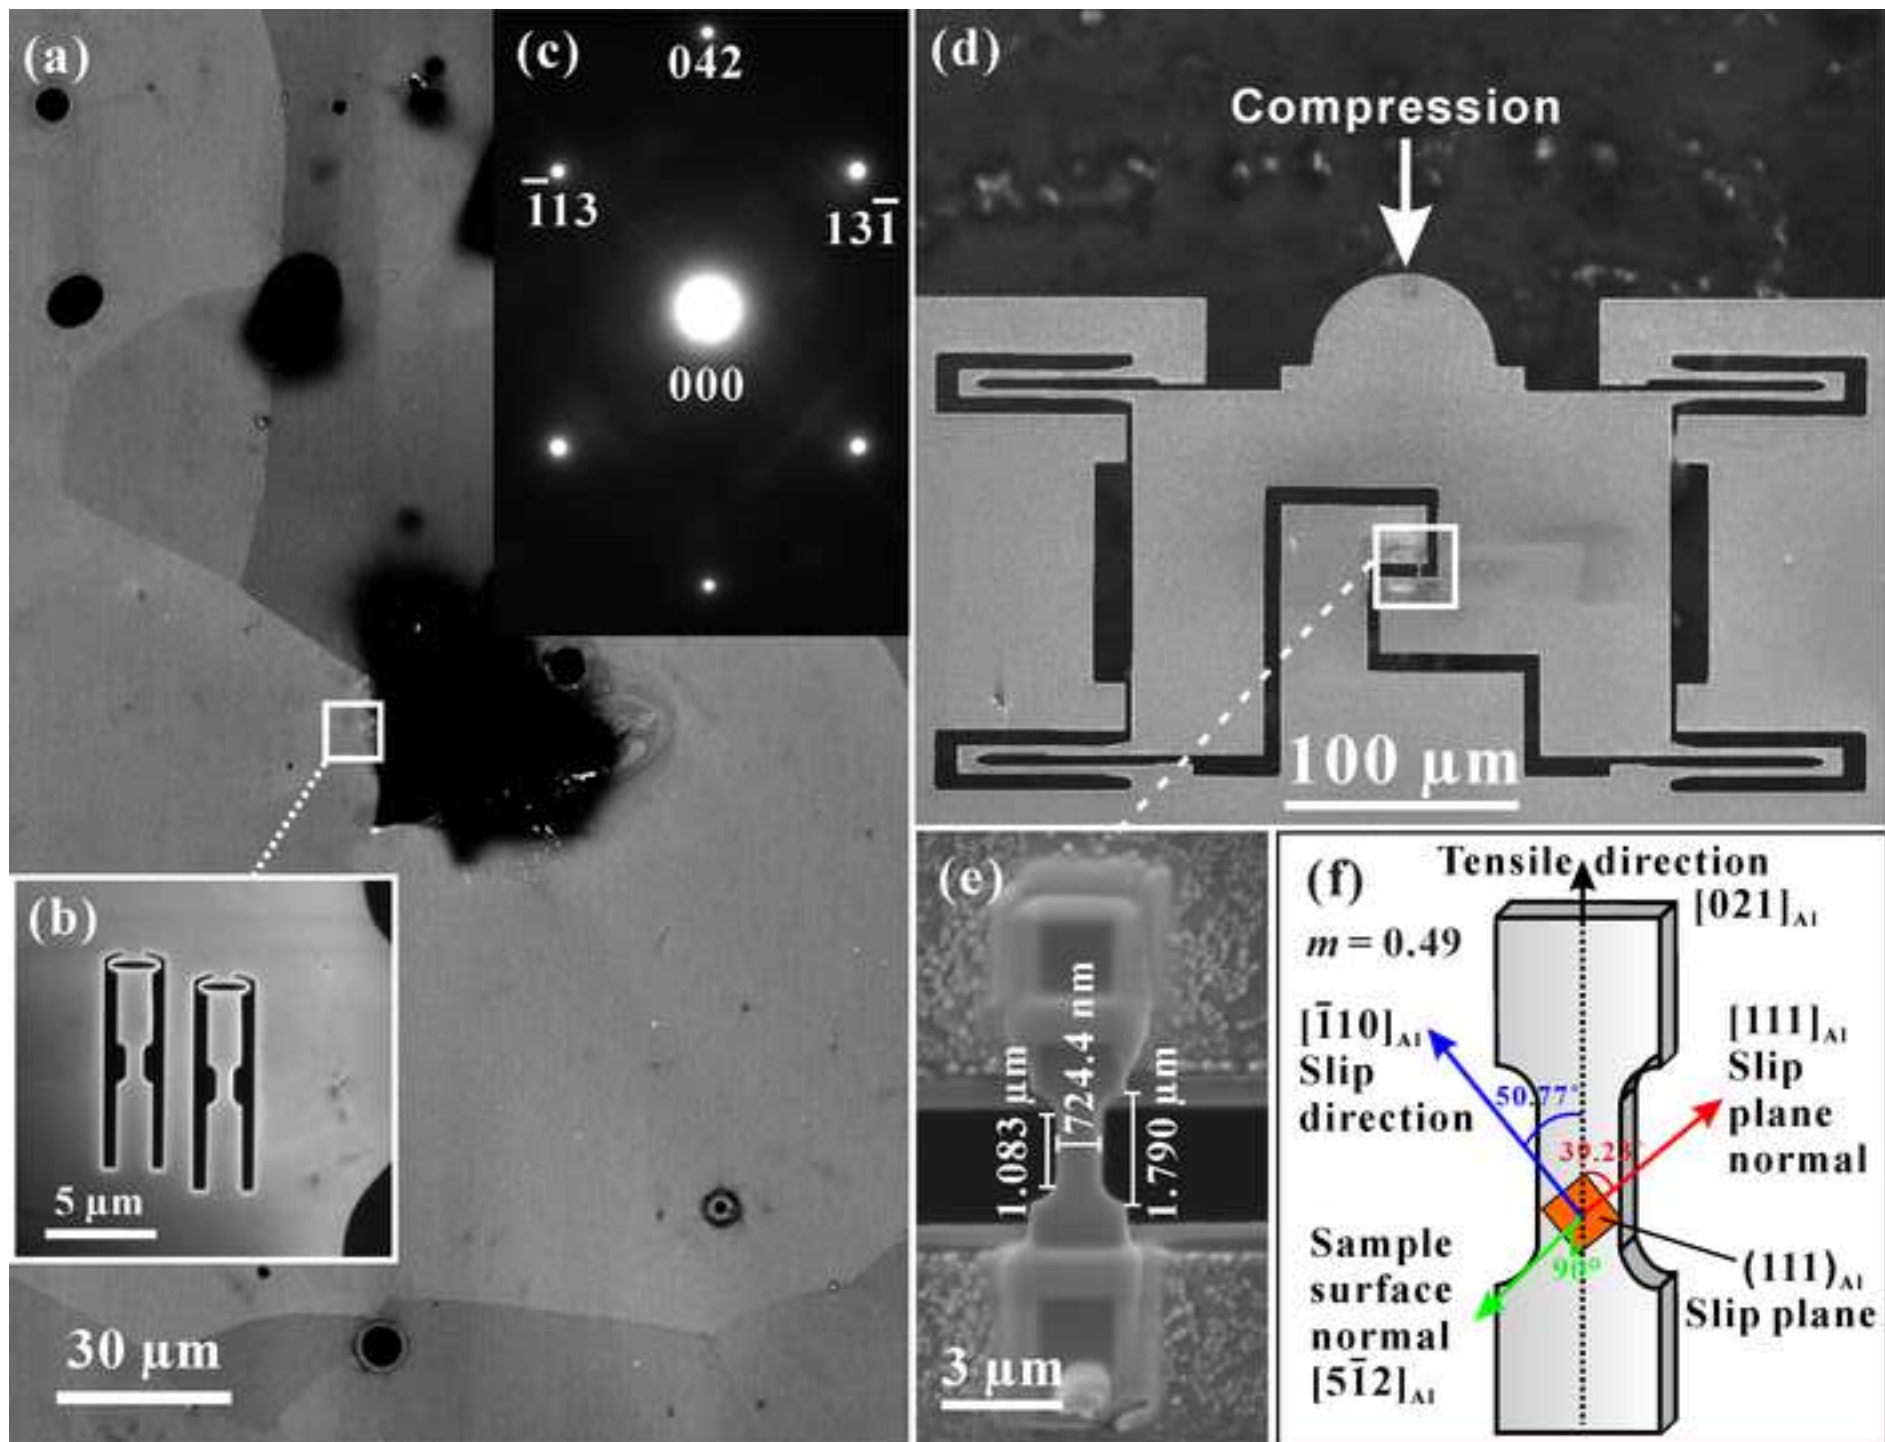


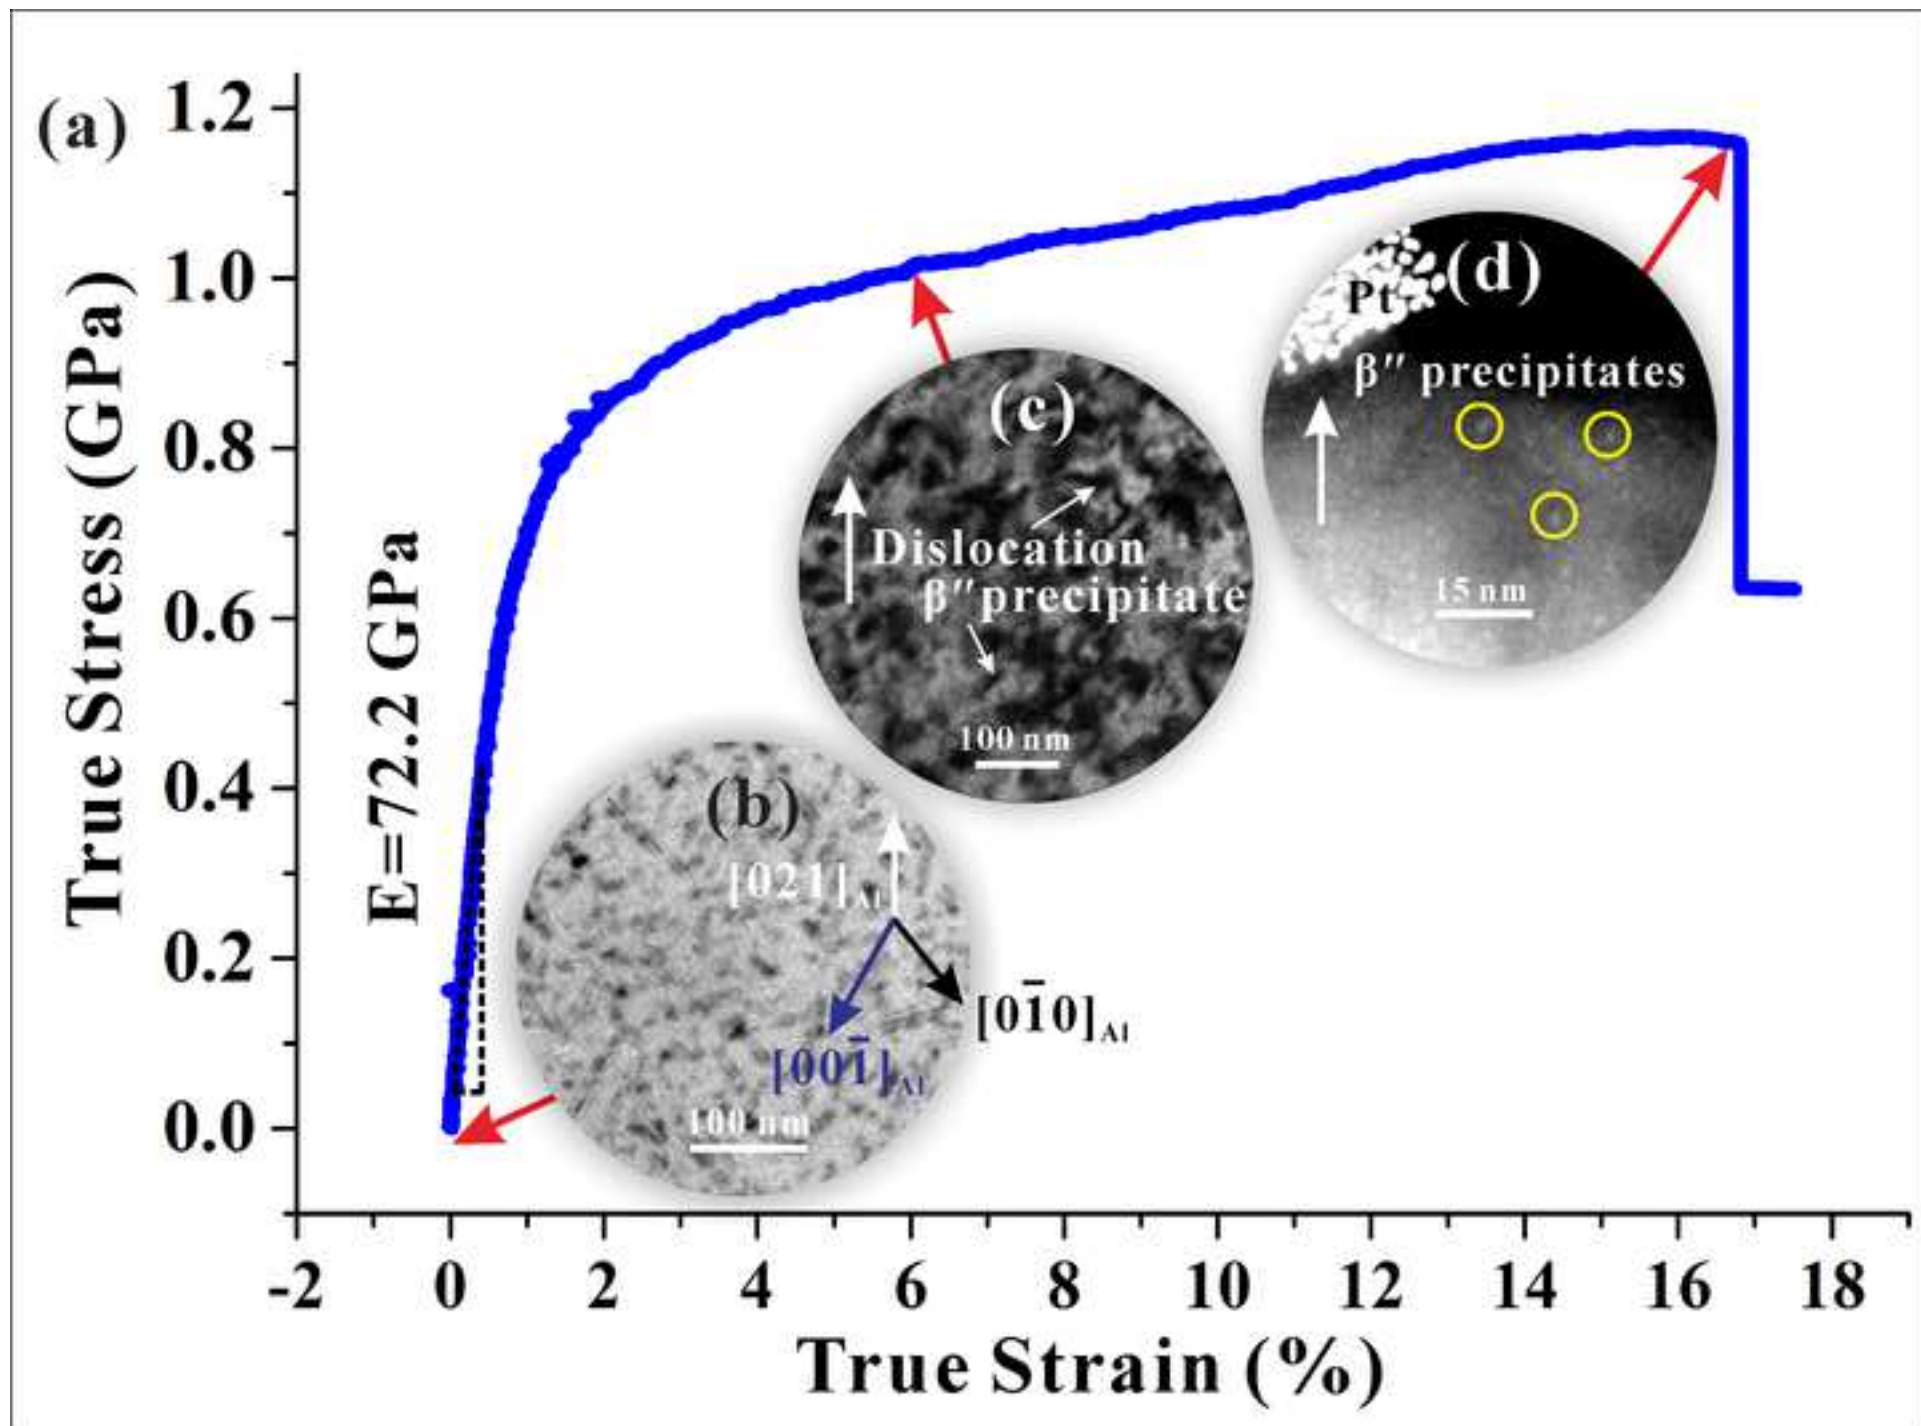


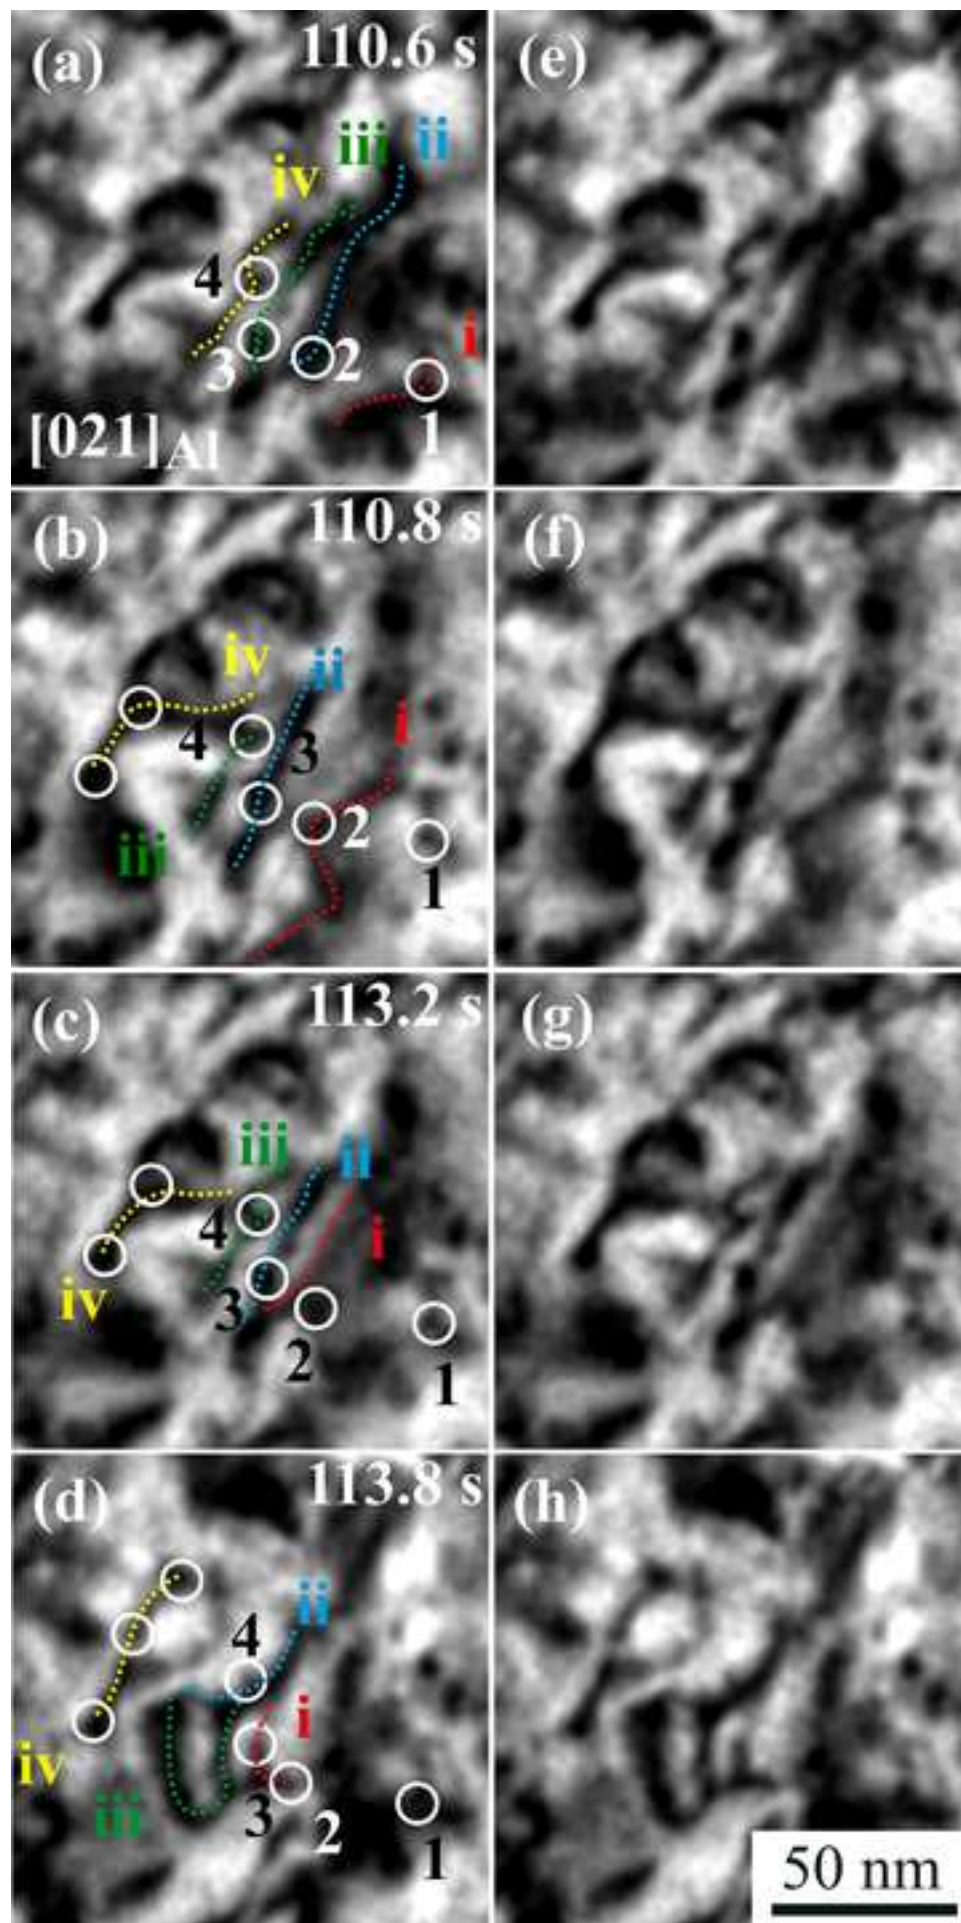




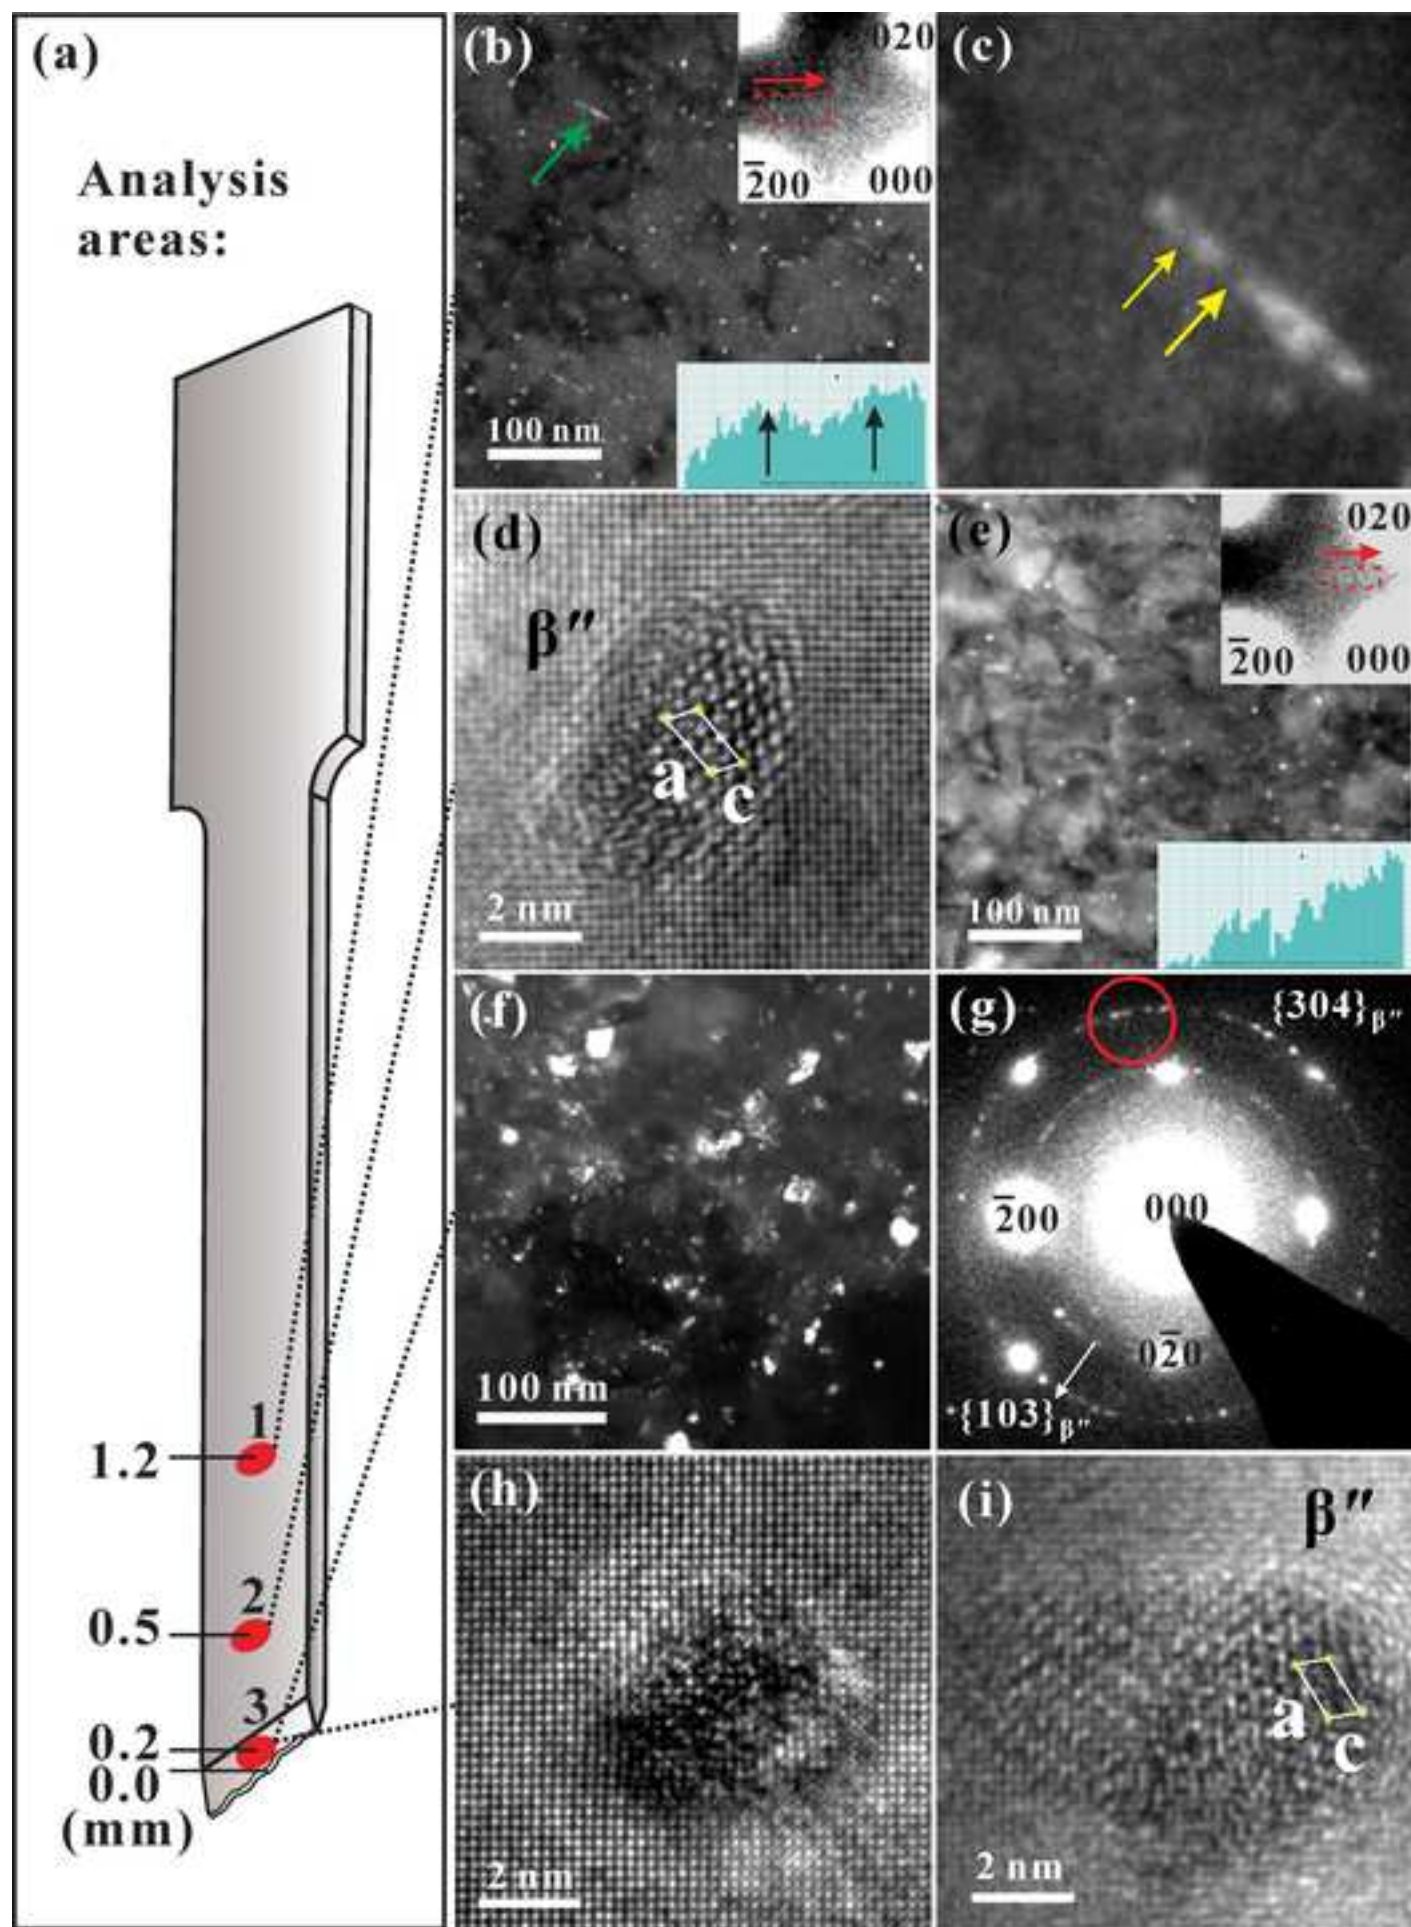


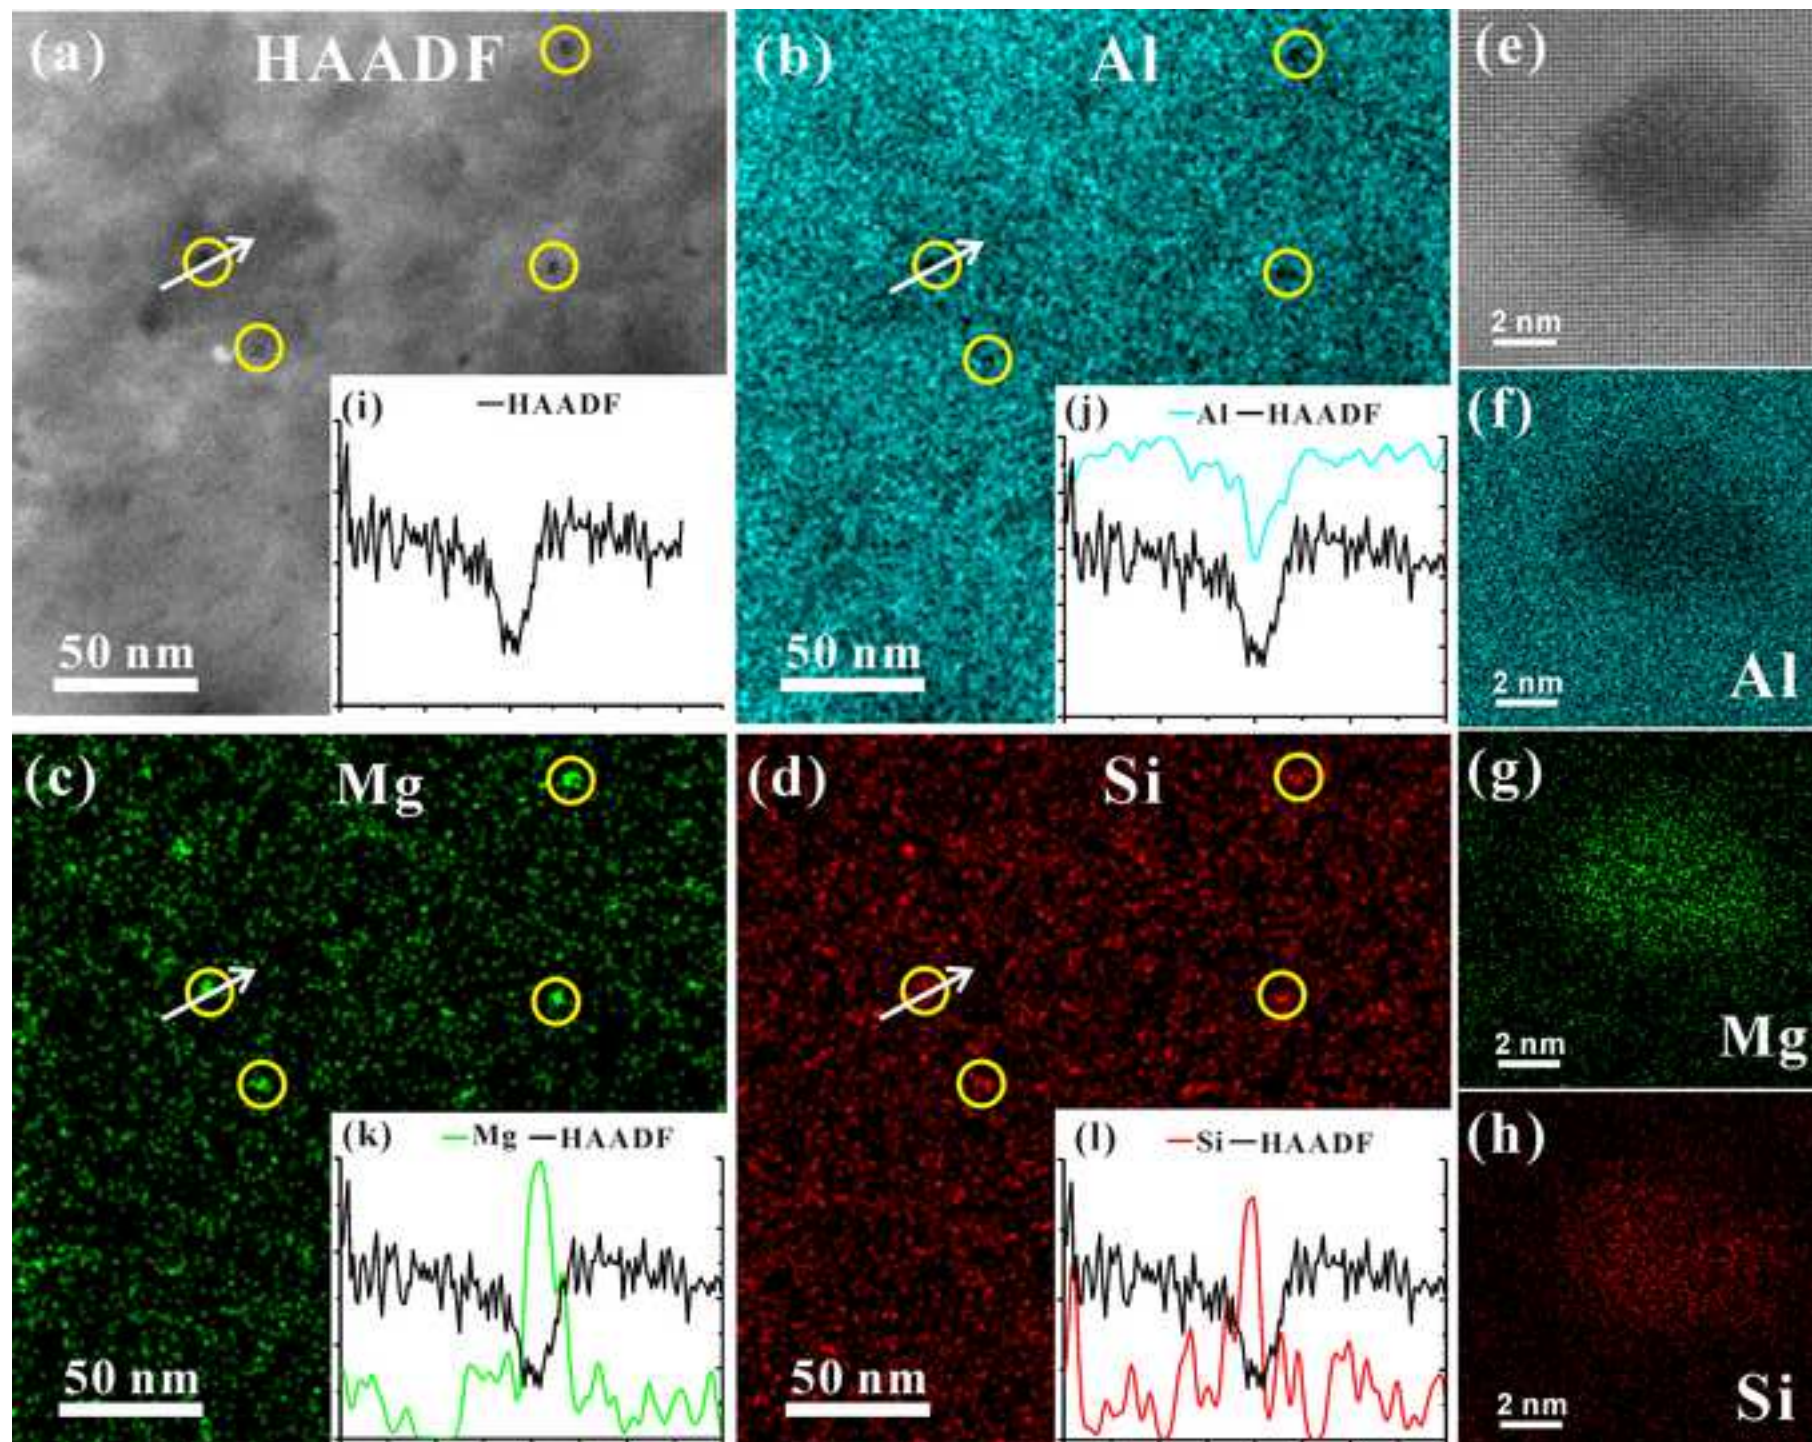


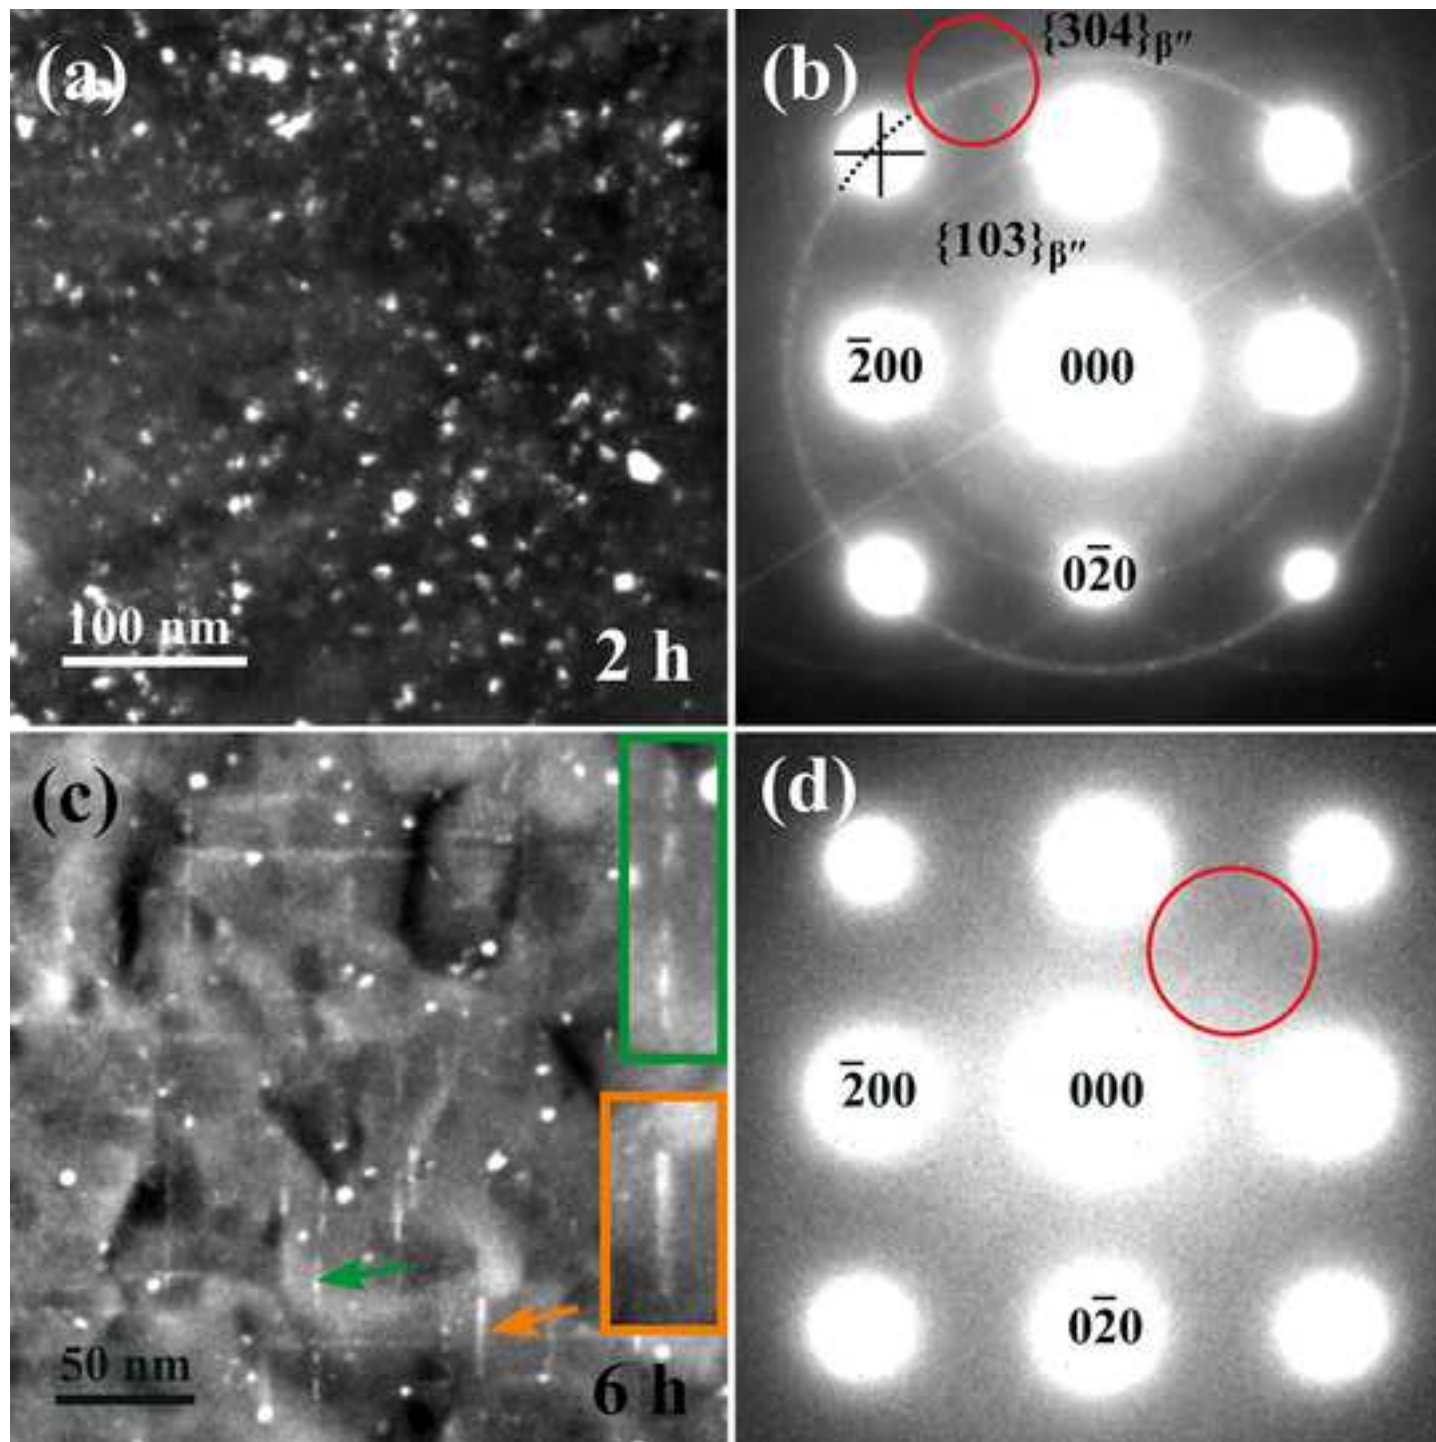

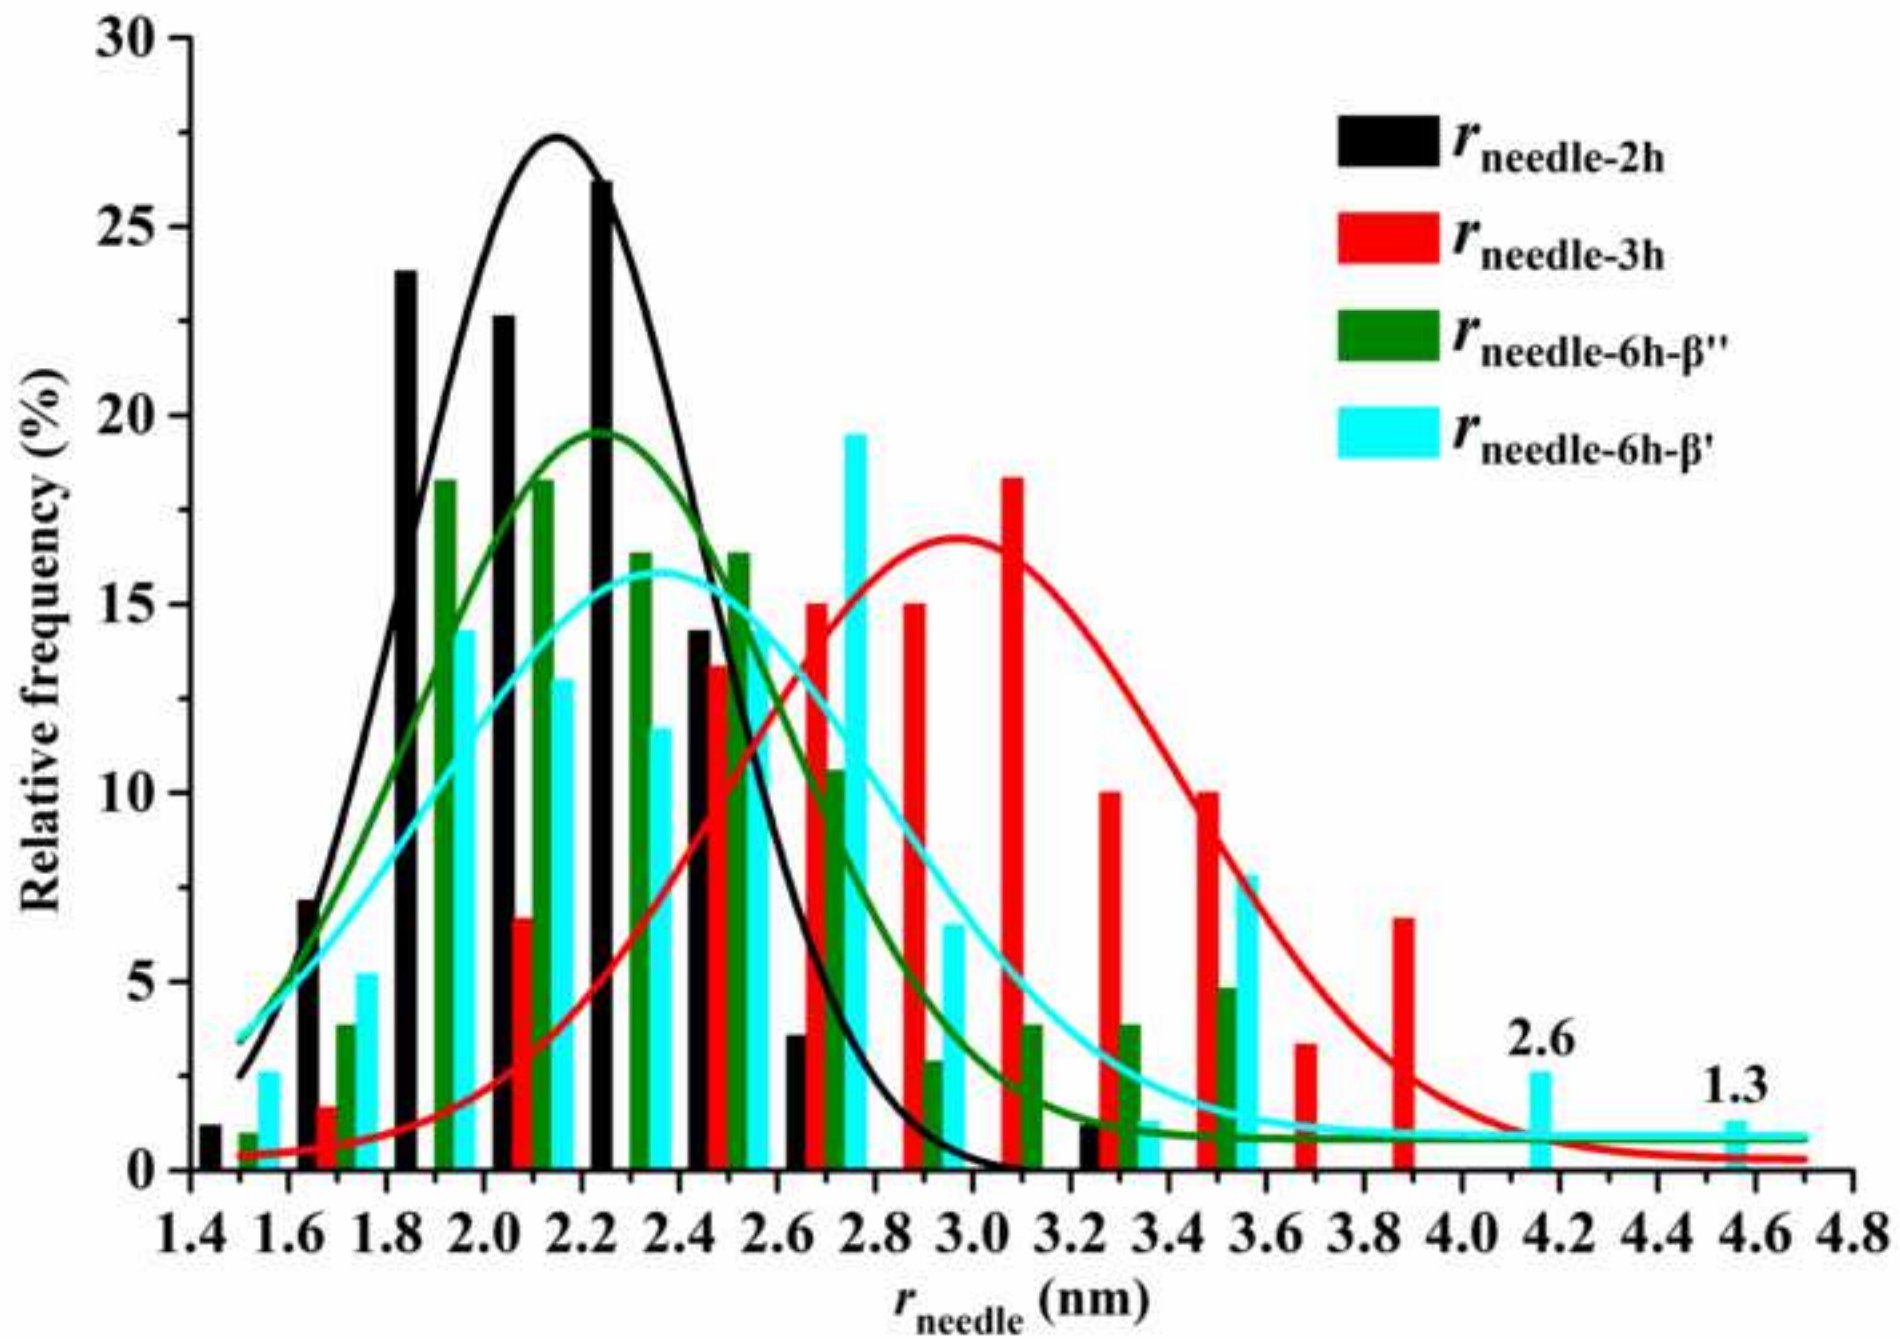

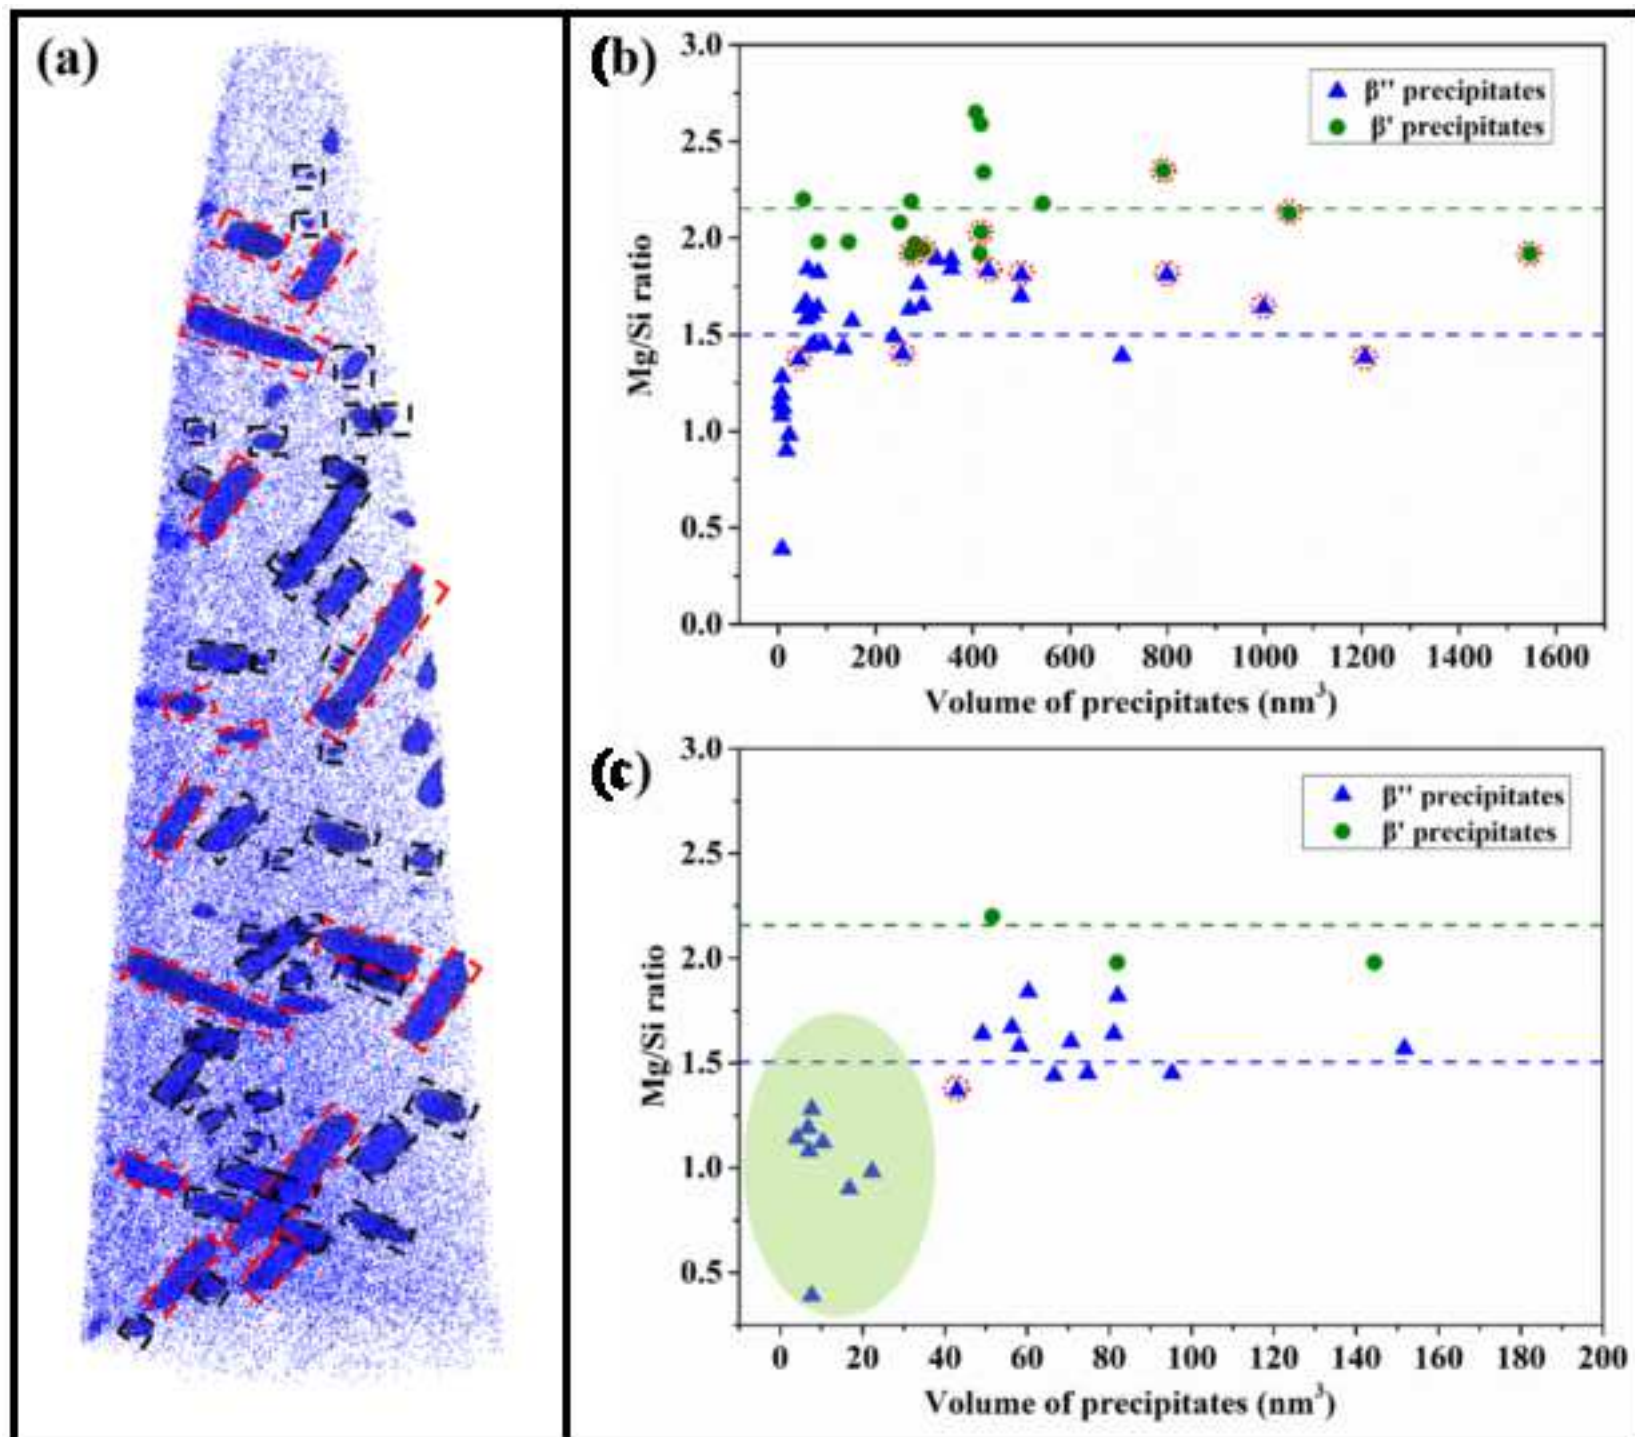

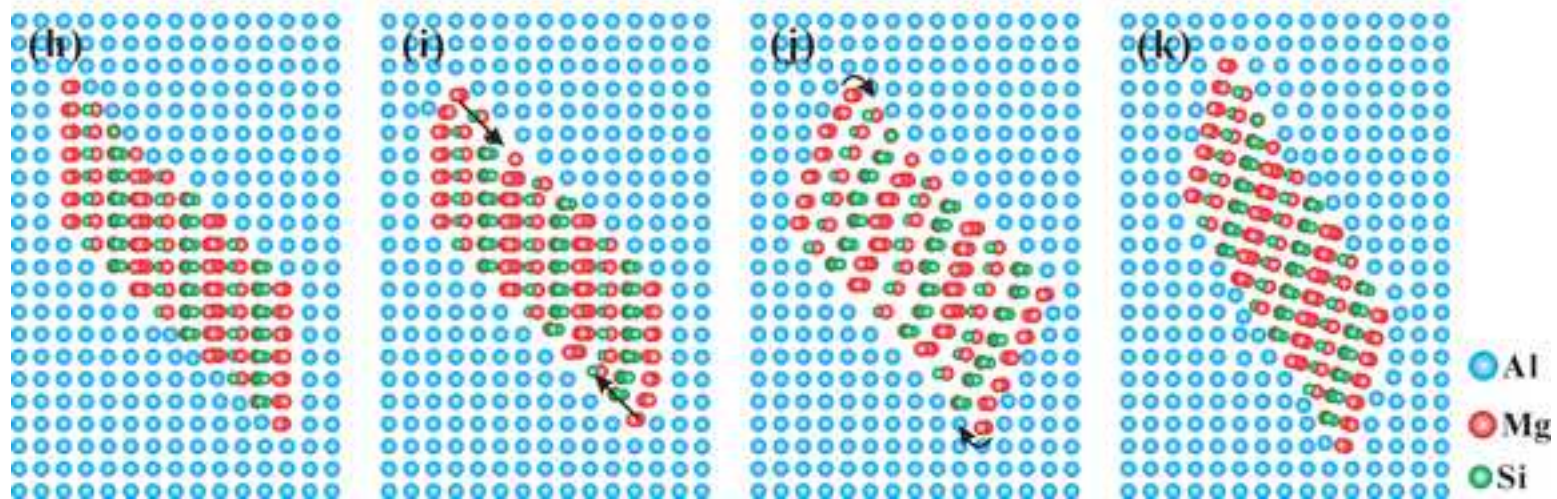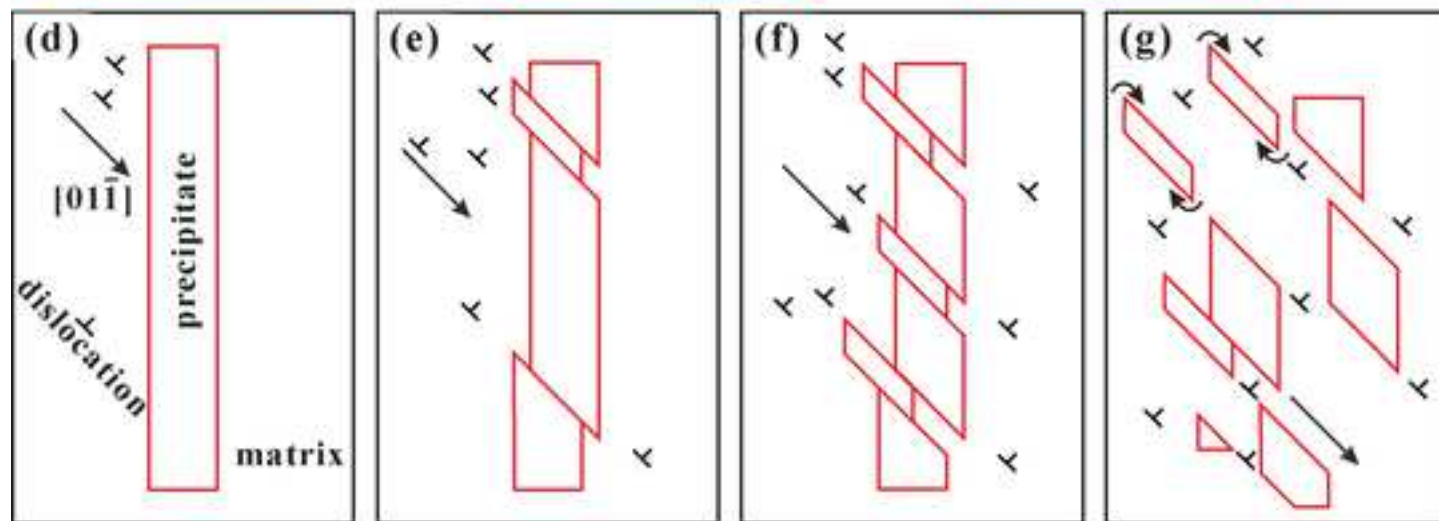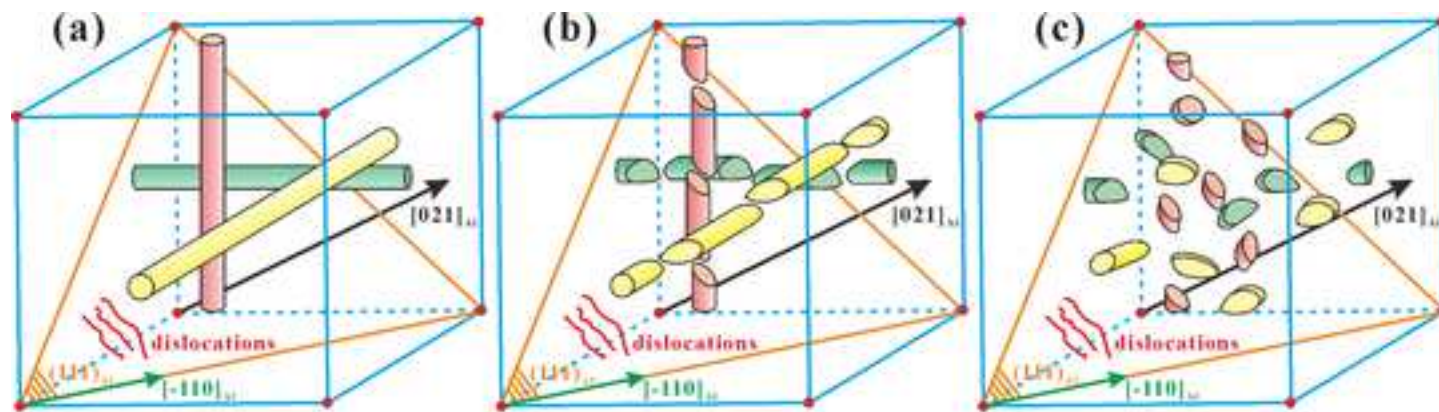




Click here to access/download
Supplementary Material
Supplemental Material (SM).docx







Click here to access/download
Supplementary Material
Raw Data for figures.rar



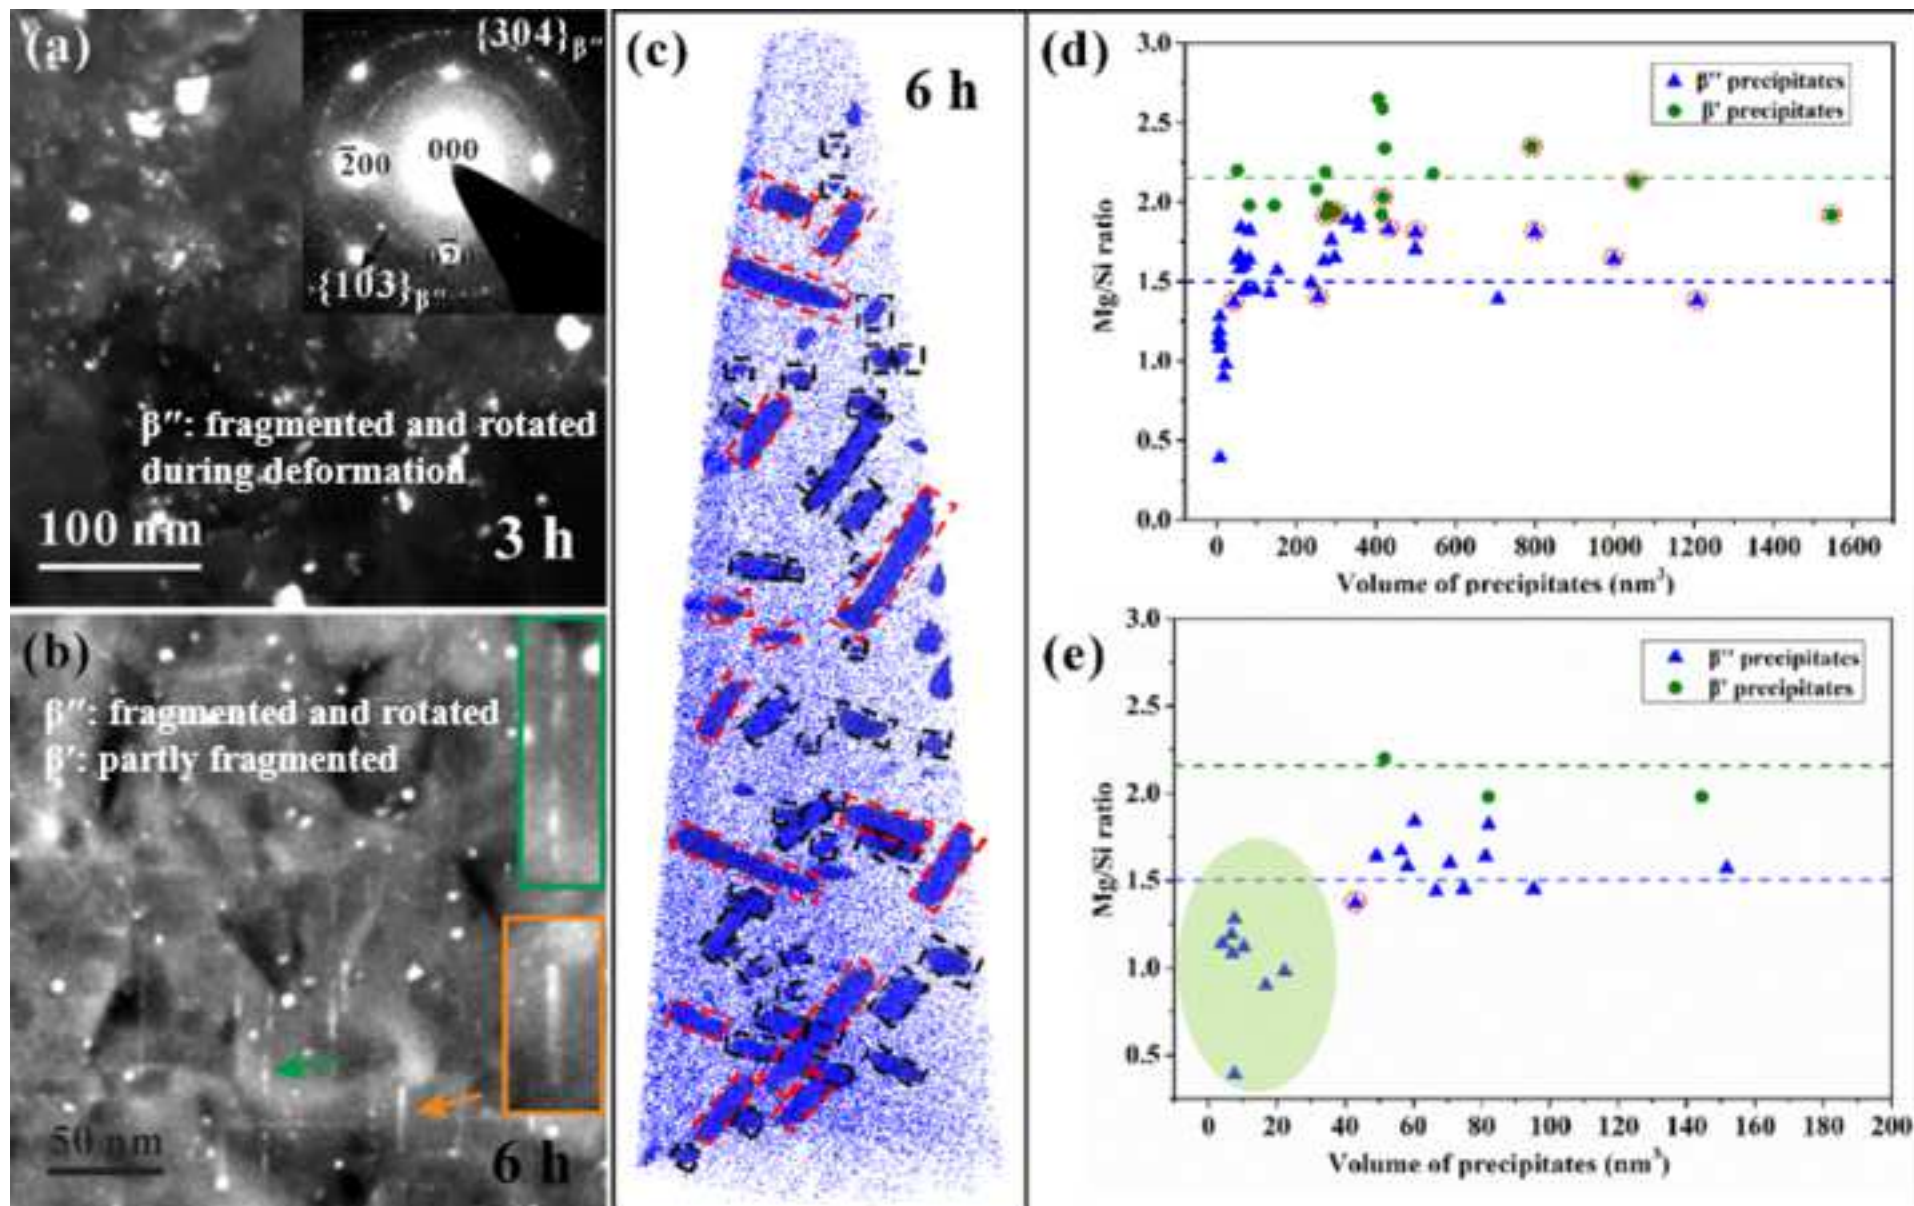



Click here to access/download
Video Still
Supplementary video 1.mov





Click here to access/download
Video Still
Supplementary video 2.mov



Declaration of interests

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: